

AD-A121 545

MASS SPECTROMETRIC THERMAL DECOMPOSITION AND
ULTRAVIOLET IRRADIATION STUD. (U) SPACE SCIENCES INC
MONROVIA CA M FARBER ET AL. SEP 82 N00014-80-C-0711

1/1

UNCLASSIFIED

F/G 7/4


NL

END

FILMED

1

DTIC

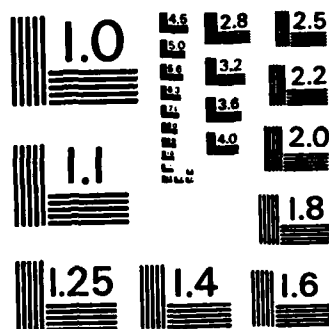

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

SPACE SCIENCES, INC.

135 WEST MAPLE AVENUE • MONROVIA, CALIFORNIA 91016 • [213] 357-3879

MASS SPECTROMETRIC THERMAL DECOMPOSITION AND ULTRAVIOLET IRRADIATION STUDIES OF SOME AZIDO AND NITRATO POLYMERIC BINDERS

Milton Farber, S. P. Harris and R. S. Srivastava

ANNUAL SUMMARY REPORT

Department of the Navy
Office of Naval Research
Arlington, Virginia 22217

Contract N00014-80-C-0711

September 1982

DTIC
ELECTE
NOV 15 1982
A

Approved for public release; distribution unlimited.
Reproduction in whole or in part is permitted for
any purpose by the United States Government.
This research was sponsored by the Office of Naval
Research.

AD A121545

DTIC FILE COPY

42 11 11 050

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO. <i>AD-A121545</i>	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Mass Spectrometric Thermal Decomposition and Ultraviolet Irradiation Studies of some Azido and Nitrate Polymeric Binders		5. TYPE OF REPORT & PERIOD COVERED Annual Summary 1 Aug 1981 - 31 July 1982
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) Milton Farber, S. P. Harris, R. D. Srivastava		8. CONTRACT OR GRANT NUMBER(s) N00014-80-C-0711
9. PERFORMING ORGANIZATION NAME AND ADDRESS Space Sciences, Inc. 135 W. Maple Ave. Monrovia, CA 91016		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Code 432 Arlington, Virginia 22217		12. REPORT DATE September 1982
		13. NUMBER OF PAGES 39
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) <div style="display: flex; justify-content: space-between;"> <div> bis azido methyl oxetane (BAMO) azido methyl methyl oxetane (AMMO) azido oxetane (AZOX) bis nitrate methyl oxetane (DNAO) copolymers </div> <div> thermal decomposition activation energies mass spectrometry ultraviolet irradiation </div> </div>		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Thermal decomposition studies were conducted on AZOX and AMMO homopolymers and on 50-50% BAMO-AZOX and 50-50% BAMO-AMMO copolymers. Decomposition was initiated at approximately 120 C, with activation energies for the materials approximately 170 kJ mol⁻¹. The primary mechanism for the decomposition is the release of molecular N₂. Backbone decomposition occurs at temperatures above 150 C		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 68 IS OBSOLETE


UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

with thermal destruction of the three-carbon chain. A thermal decomposition study of a new copolymer consisting of an azido (BAMO) and nitrate ester, bis nitrate methyl oxetane (DNAO) showed both azide and nitrate group decomposition at differing rates. Preliminary mass spectrometric studies of the decomposition of a new amino nitro ring compound, $C_6H_8N_8O_{12}$, indicated NO_2 release with ring stability. Qualitative UV irradiation experiments at 2540 Å and 3660 Å wave lengths then were conducted on AZOX and AMMO homopolymers and 50-50% BAMO-AMMO and 50-50% BAMO-AZOX copolymers. Upwards of 25% of the polymeric N_2 was released with considerable cross-linking. The samples changed from viscous liquids to gummy, rubbery semi-solids. The irradiated samples were maintained for a number of weeks under ordinary atmospheric conditions as well as under vacuum without any indication of autocatalysis.

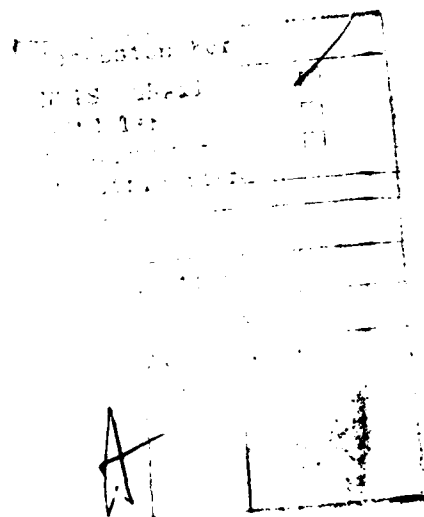

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

I. INTRODUCTION

Thermal decomposition studies on azido polymers were continued during the past twelve months. Also, the thermal decomposition of a newly prepared energetic nitro amine ring compound from the Naval Surface Weapons Center, White Oak, was investigated. The azido materials studied included BAMO, AMMO, AZOX and DNAO polymers and copolymers supplied by SRI International.

The experimental program consisted of two phases: the kinetic effusion-mass spectrometric studies on the polymeric materials and the new amino nitro ring compound, and qualitative ultraviolet decomposition measurements on the azido polymers.


The Annual Summary Report dated September 1981 presented the results of thermal decomposition studies on the homopolymers of BAMO and GAP and monomeric AZOX.

II. MASS SPECTROMETER STUDIES

A. Thermal Decomposition of Azido Polymers

1. AZOX

In order to obtain reliable thermal decomposition kinetics it was imperative that the polymeric samples be completely pure or that impurities such as residual solvent components be removed by low temperature heating in vacuum prior to the kinetic studies. Upon the onset of effusion-mass spectrometric investigation of the AZOX homopolymer

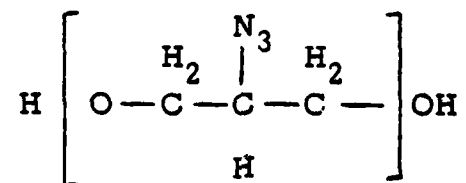

at low temperature a large concentration of ion peaks were observed in the mass spectra. For example, Figure 1 shows these solvent products in the 27 to 32 amu range at 60 C, which nearly disappear at 95 C. Similarly, Figure 2 shows these products in the 38 to 45 amu range at 80 C, with their virtual disappearance when the temperature has reached 100 C. These

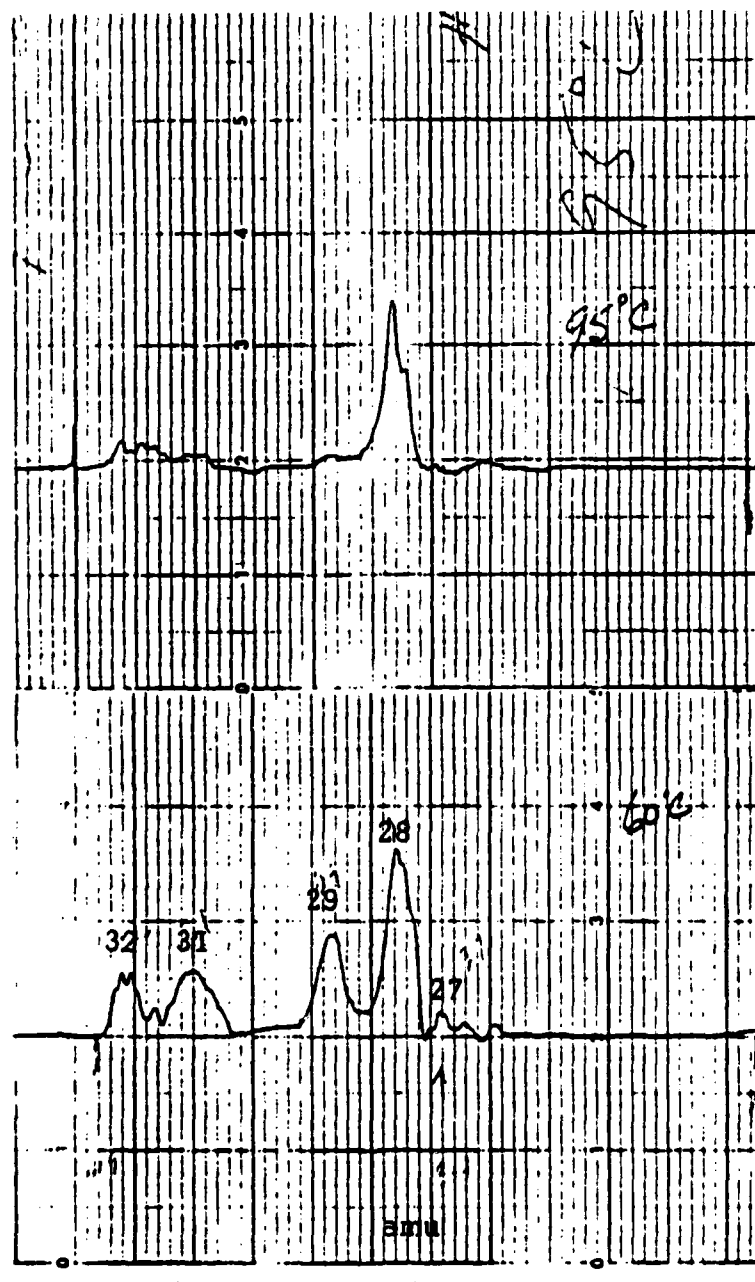


Fig. 1. Solvent products recorded by the mass spectrometer while studying the thermal decomposition of AZOX homopolymer. These products are seen at the lower temperatures, approximately 60 C, and disappear or are greatly reduced as the temperature reaches 95 C.

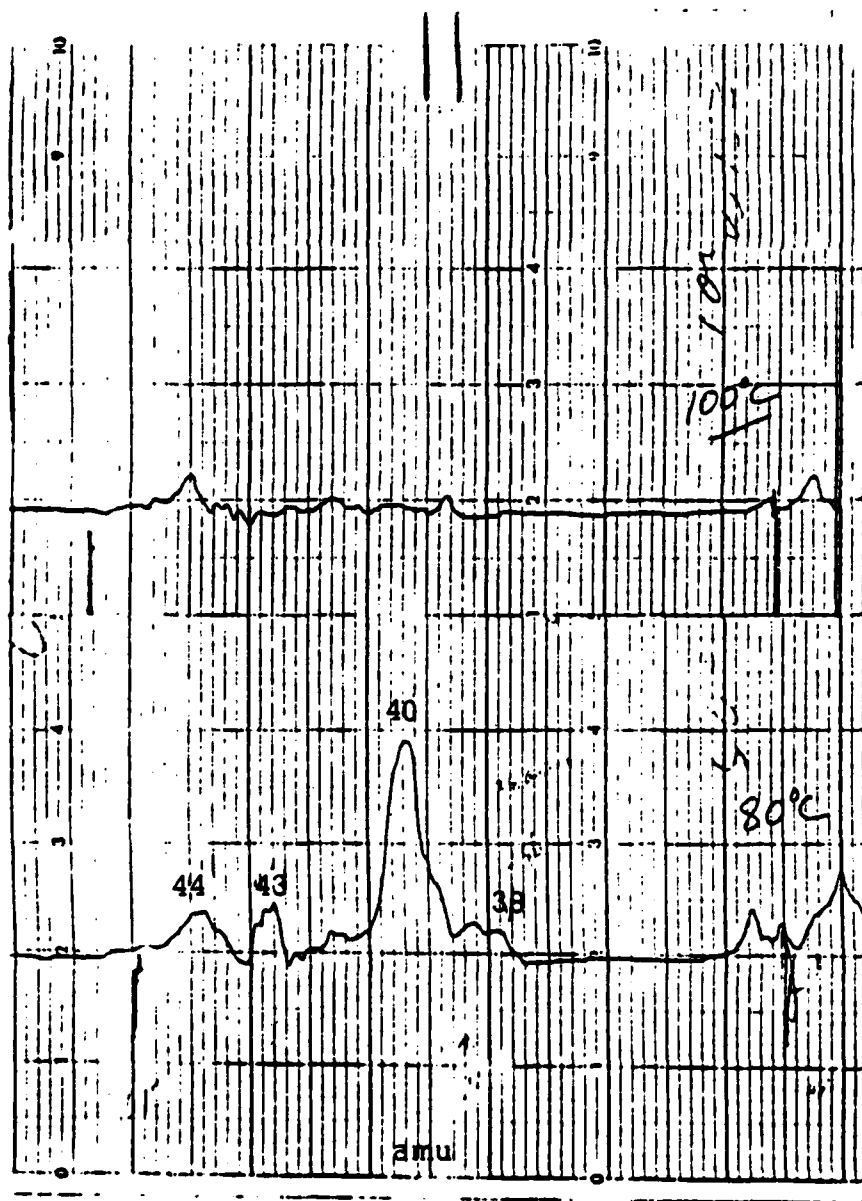



Fig. 2. Solvent products recorded by the mass spectrometer while studying the thermal decomposition of AZOX homopolymer. Although the products appear at the lower temperatures, approximately 80 C, they have disappeared at 100 C.

temperatures are below the temperature of the onset of thermal decomposition of the AZOX polymer.

After heating the AZOX homopolymer samples until the mass spectra indicated no further impurities the kinetic studies were commenced. As in previous azido polymers, molecular N_2 was the first thermal decomposition product occurring at approximately 120 C. Figure 3 shows the mass spectra of the thermal decomposition from 160 to 195 C. In this 35-degree range the N_2 intensity increased by a factor of 20. In Figure 3 the amu range is 24 to 32. The central peaks are molecular nitrogen, with smaller peaks on each side of HCN at 27 amu and HCO at 29 amu. These graphs are composites of the individual peak heights and are not continuous as a function of temperature. By plotting the log of the N_2 intensity against the reciprocal of the absolute temperature (Fig. 4) an activation energy, E_a , of $167.8 \text{ kJ mol}^{-1}$ (40.1 kcal/mole) is obtained. As the temperature is raised the three-membered carbon backbone of AZOX begins to disintegrate with the ion spectra showing the species CH_2 , CH_3 , OH , and H_2O in the low mass range. The higher amu range shows peaks attributed to CO , CH_2OH , C_2OH , and CO_2 at 230 C (Fig. 5). A small ion intensity has been attributed previously to HN_3 at amu 43.

2. AMMO

The thermal decomposition of a relatively new azide polymer, AMMO, (azido methyl methyloxetane)

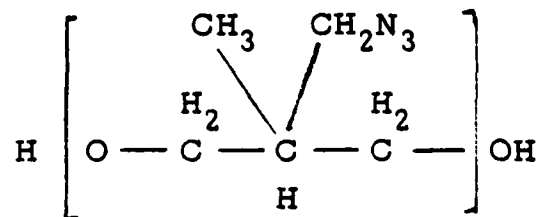

was initiated. This polymer is similar to BAMO (the bis azido methyl oxetane) except that it has one azido methyl group on the center carbon of the three-carbon backbone, whereas BAMO has two.

AMMO was found to have a somewhat higher stability than the other azide polymers. A study of N_2 evolution, which is the

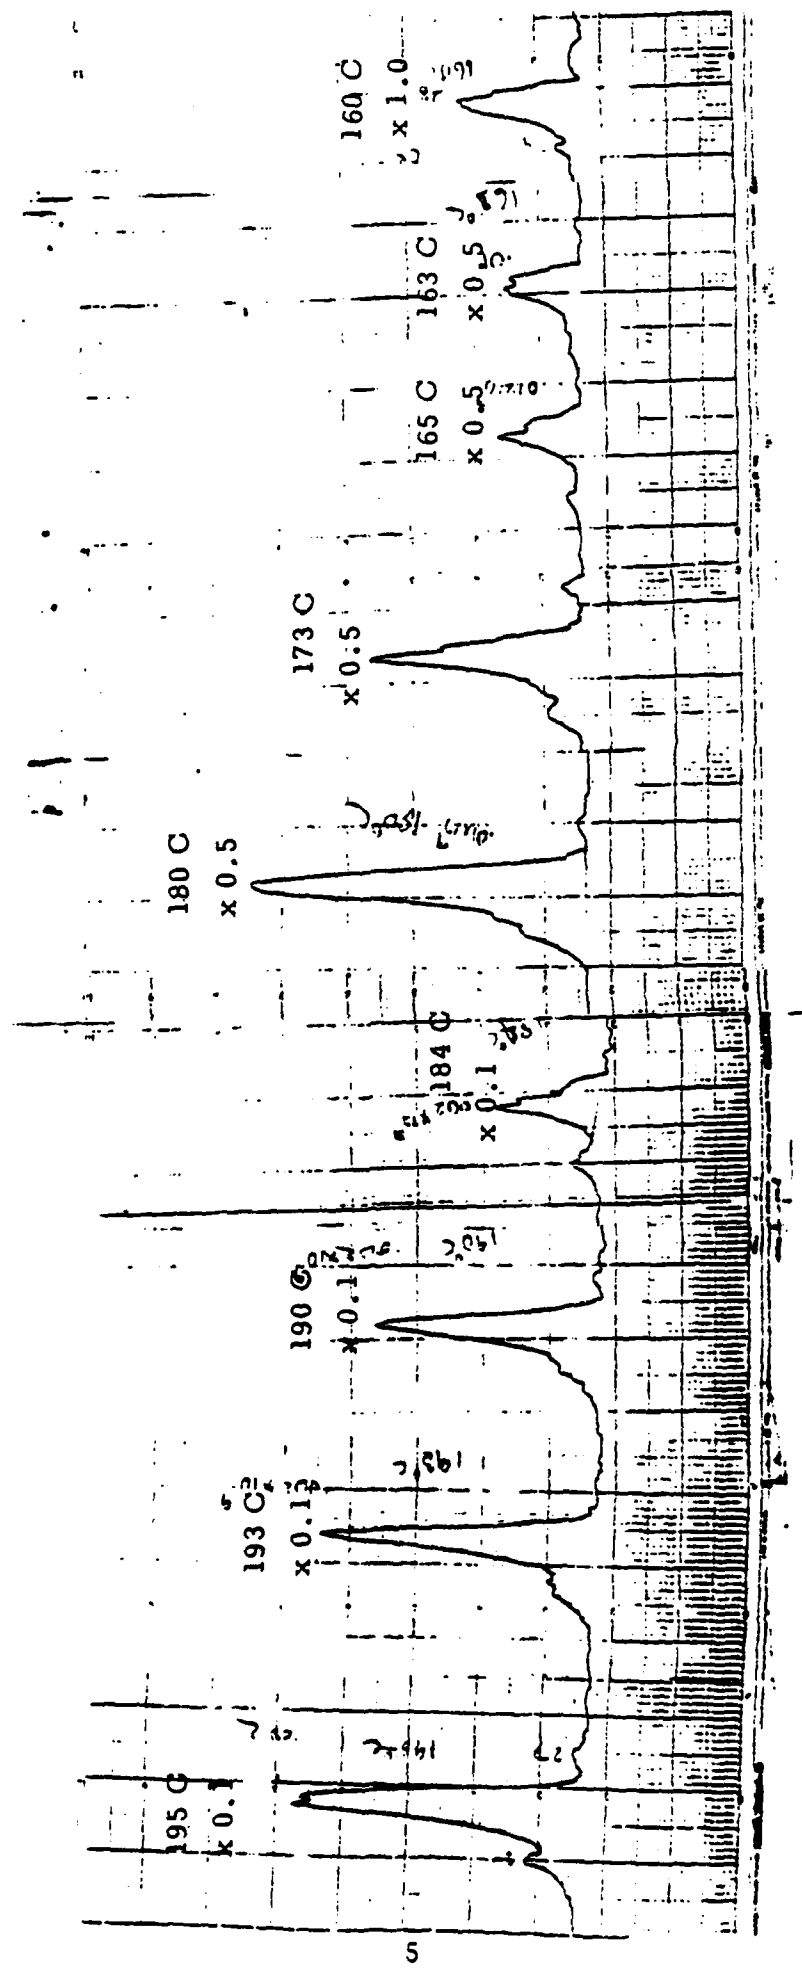


Fig. 3. Decomposition of AZOX monomer as a function of temperature.

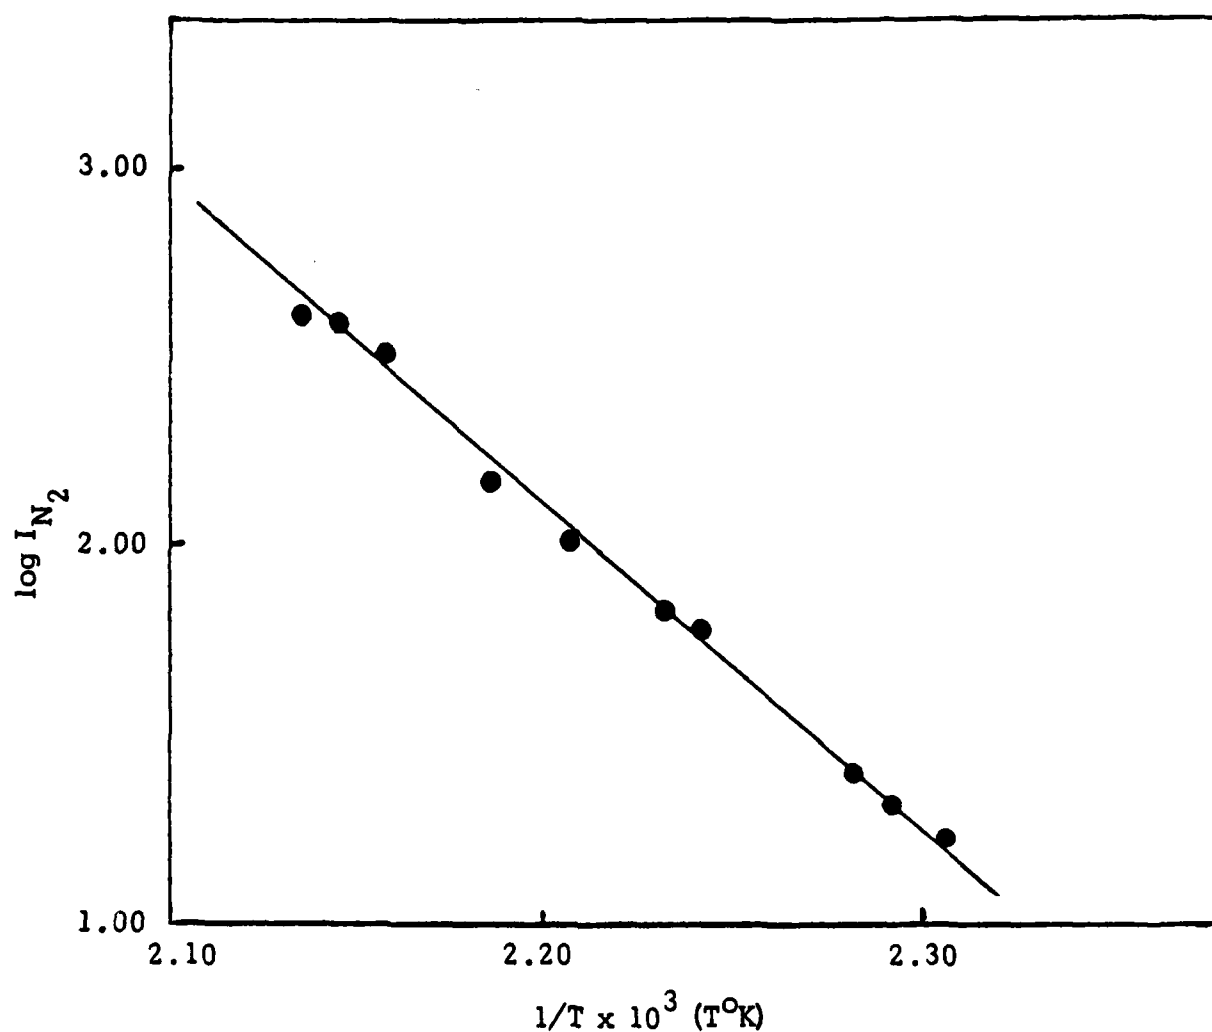


Fig. 4. Log of the relative intensity of N_2 from the thermal decomposition of AZOX plotted as a function of the reciprocal of the absolute temperature ($1/T^{\circ}K$). Activation energy = $167.8 \text{ kJ mol}^{-1}$ (40.1 kcal/mole)

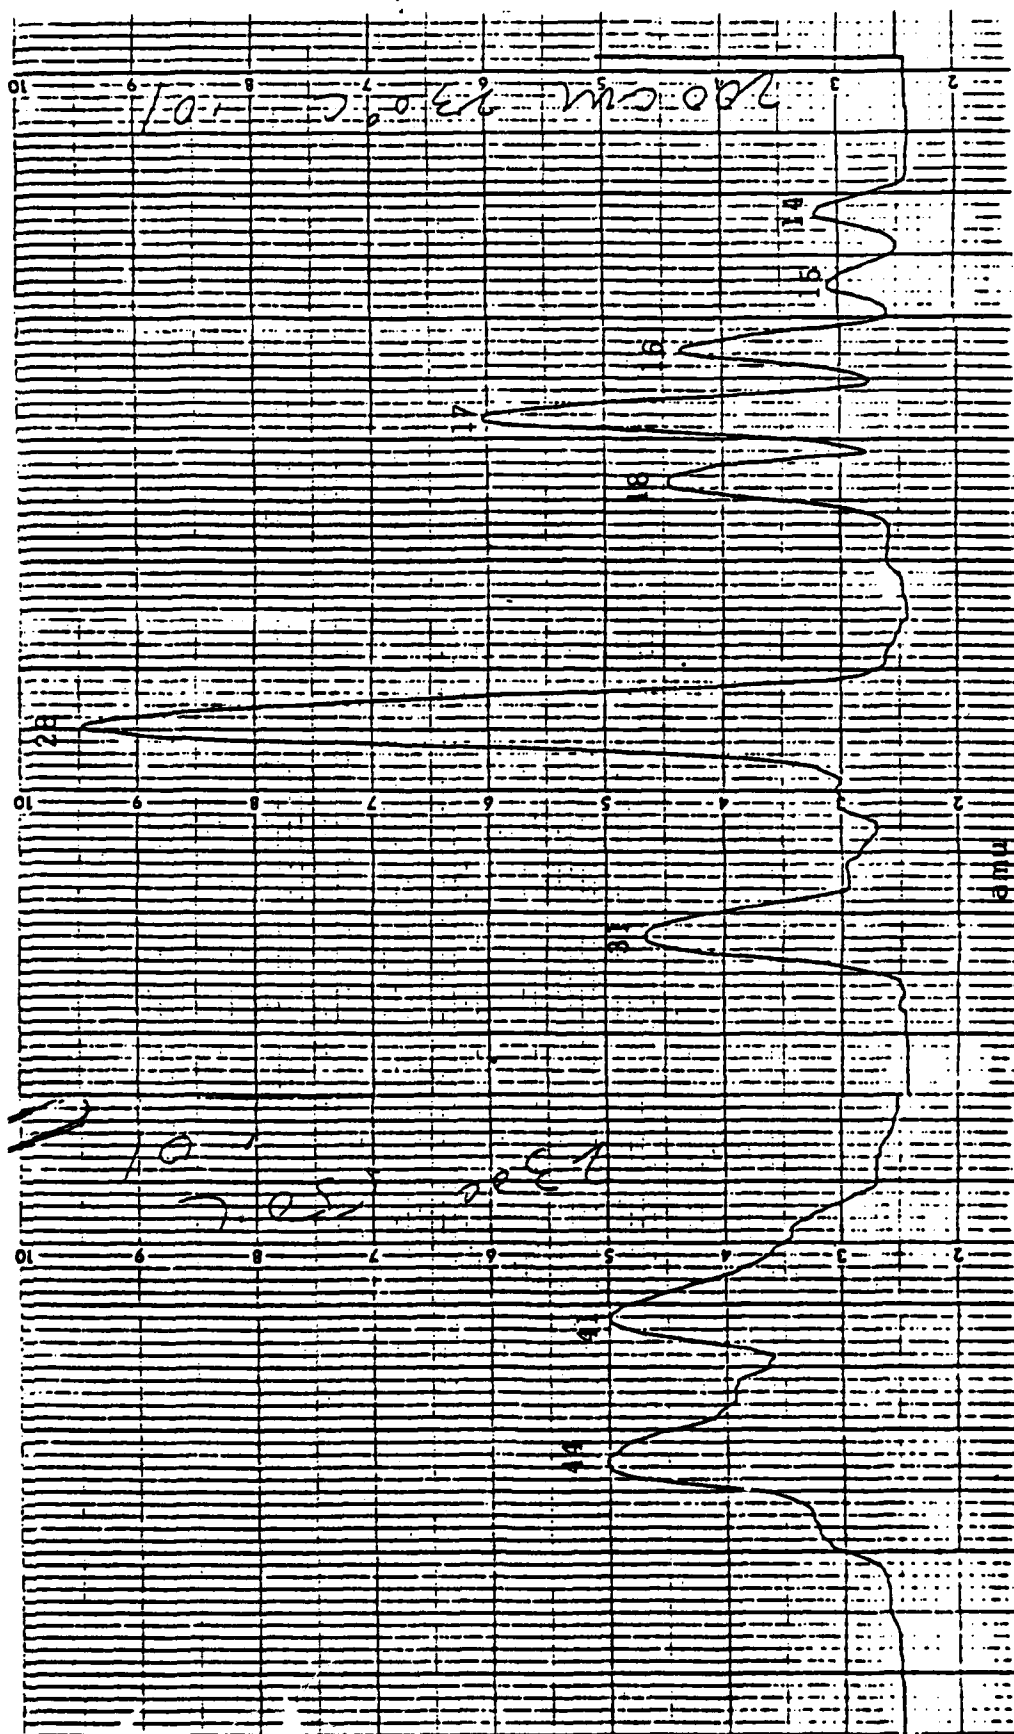


Fig. 5. Backbone decomposition of AZOX at 230 C

onset of thermal decomposition, shows that it continues until the destruction of the azide group is completed. An activation energy of 182 kJ mol^{-1} (43.6 kcal/mole) was calculated from these data. All the azido polymers, including their monomers, homopolymers and copolymers, were found to have activation energies in the range of 165 to 182 kJ mol^{-1} (40 to 43 kcal/mole). These results, based on the number of azide materials investigated, should be conclusive evidence that the polymers, copolymers, or monomers decompose primarily by the fracturing of the azide N-N bond, yielding an activation energy of approximately 164 kJ mol^{-1} (40 kcal/mole).

The thermal decomposition of AMMO was observed from 120 to 300 C. Its degree of stability can be seen in Figure 6, which shows very little backbone decomposition at 210 C. At 290 C (Fig. 7) a 30 amu peak corresponding to CH_2O indicates backbone decomposition. The relative OH and H_2O concentrations increase significantly at 290 C, as seen in Figure 7. Also, some methyl radicals at amu 15 were observed.

A qualitative indication of the relative thermal stability of BAMO and AMMO at 235 can be seen from Fig. 8.a. Considerably more H_2O is seen from the BAMO decomposition (Part B, Fig. 8.a.), indicating the release of greater quantities of OH recombining within the effusion cell to form water. Also, the relative amount of CH_3 radicals is larger from BAMO decomposition than from AMMO. As the temperature increased from 215 to 235 C (Fig. 8.b.) the thermal decomposition rate of BAMO increased rapidly, creating a fairly high cell pressure causing OH recombination to form H_2O . This does not occur with AMMO; even at temperatures as high as 290 C the OH/ H_2O ratio of AMMO appears fairly constant.

High temperature decomposition products of BAMO (Fig. 9) include mass peaks at 40, 42, 43 and 44 amu. Within the effusion cell, where numerous collisions between gaseous species and the cell walls and also with the condensed polymeric materials can occur, the probability is high that some of the products observed mass spectroscopically are produced within the effusion cell itself and are not original decomposition products from the condensed phase. The three-membered carbon backbone of BAMO is definitely beginning to disintegrate at 230 C, as seen in Figure 10, with the production of CH_2O and CH_2OH at amu values of 30 and 31. The

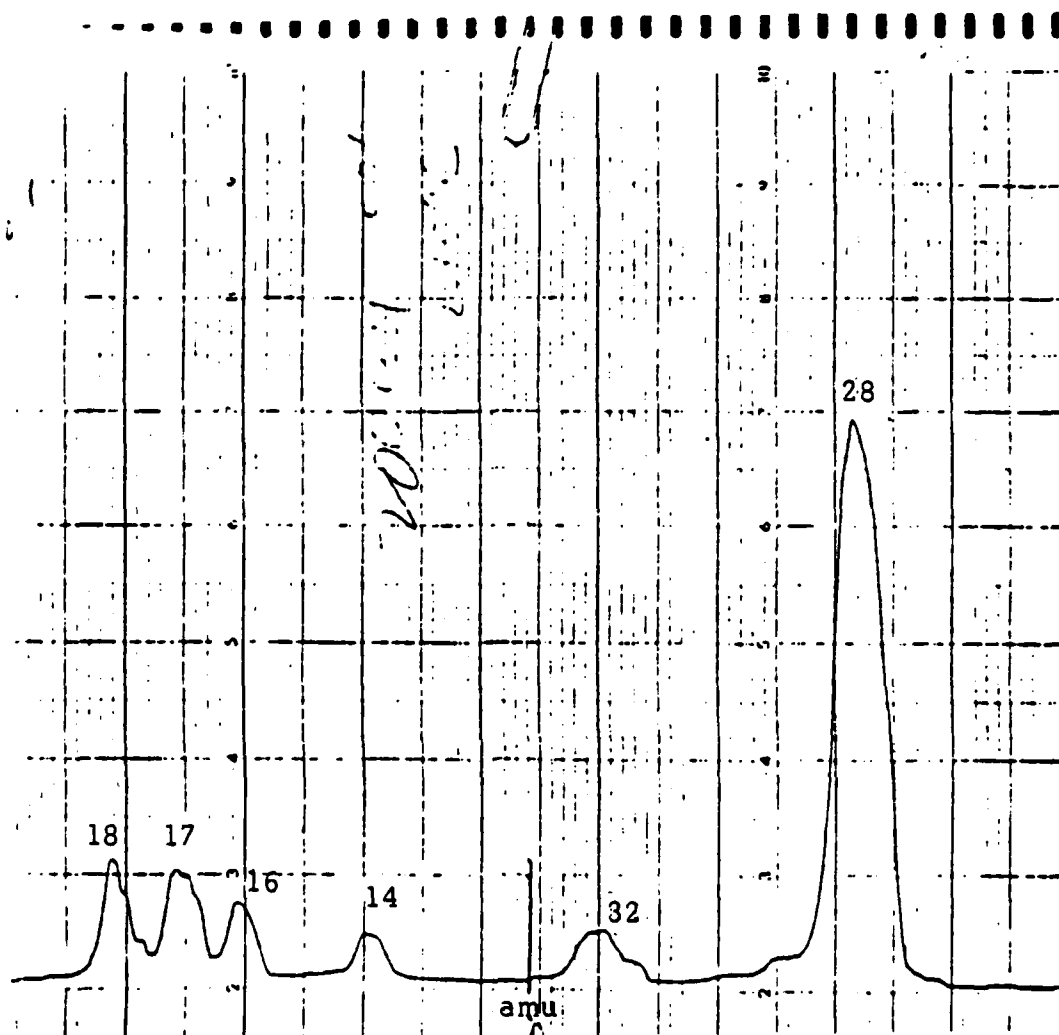


Fig. 6. Thermal decomposition of AMMO at 210 C.

The azide group is decomposing, with the release of N_2 and some end group decomposition taking place; OH and H_2O peaks are observed at amu 17 and 18.

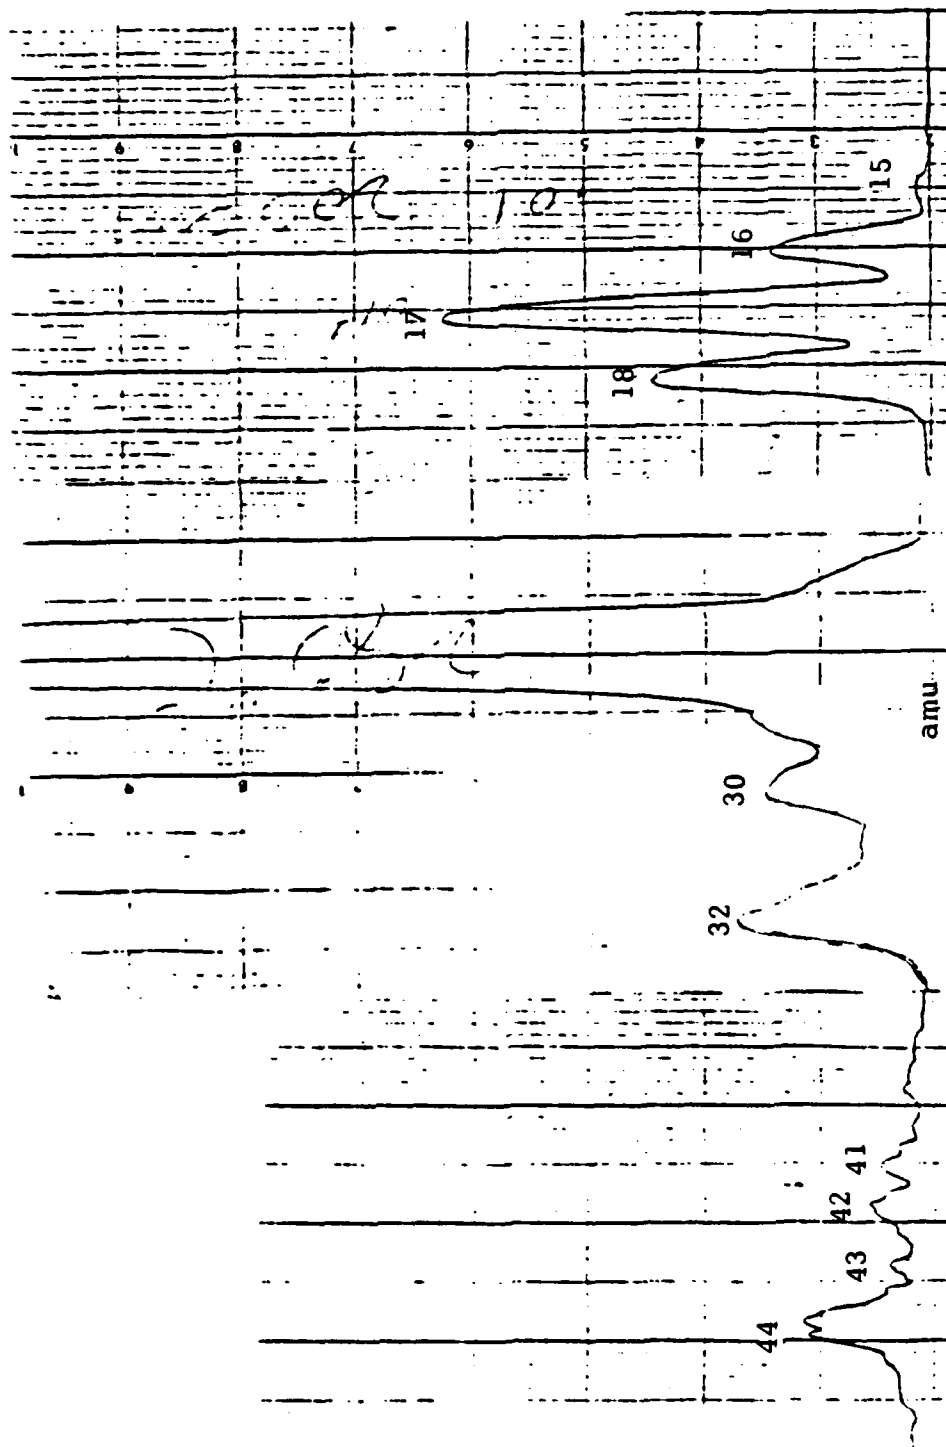


Fig. 7. AMMO products at 290 C in three amu ranges showing disintegration of the backbone

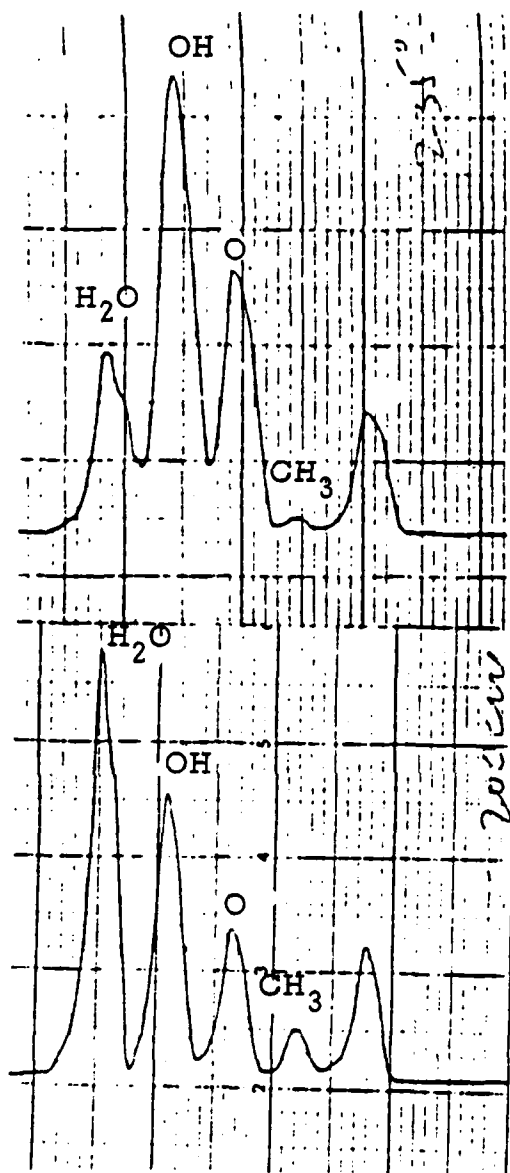


Fig. 8.a. Thermal decomposition comparison of AMMO (Part A) and BAMO (Part B) showing relative peaks of OH, H_2O and CH_3

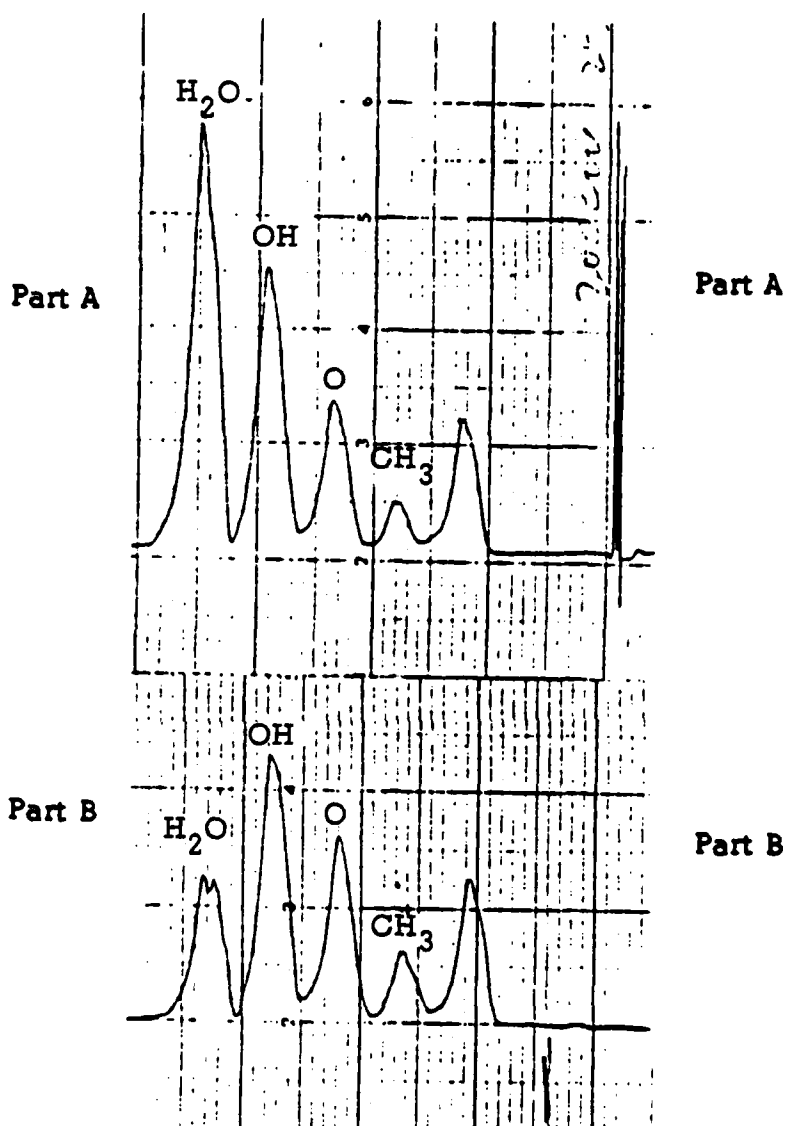


Fig. 8.b. Thermal decomposition comparison of BAMO at 235 C (Part A) and 215 C (Part B) showing the reversal of the relative concentration of OH and H_2O at 215 and 235 C

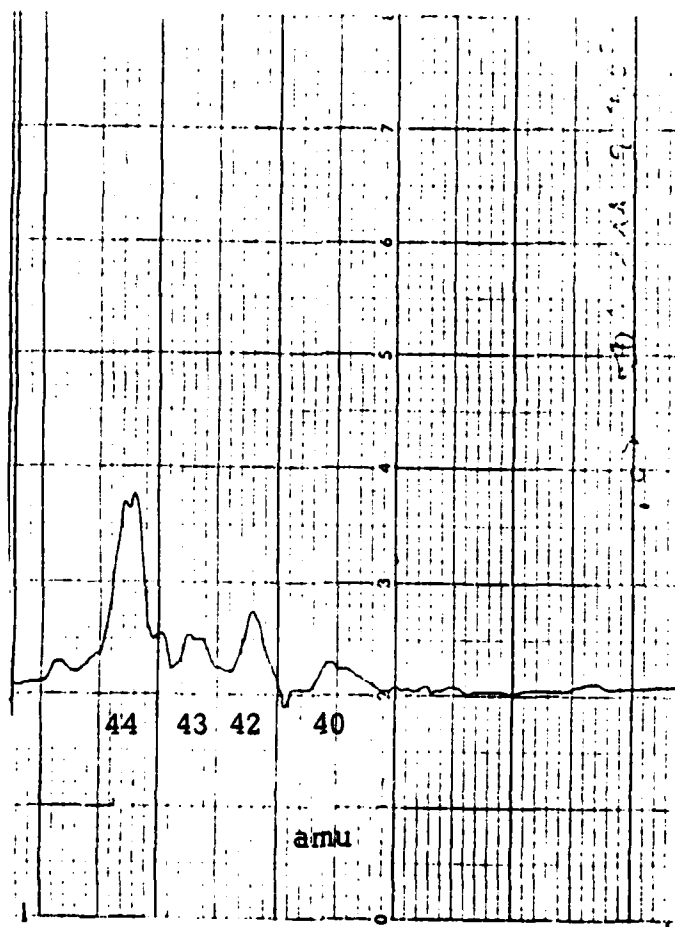


Fig. 9. BAMO products at 230 C in the 40 amu range

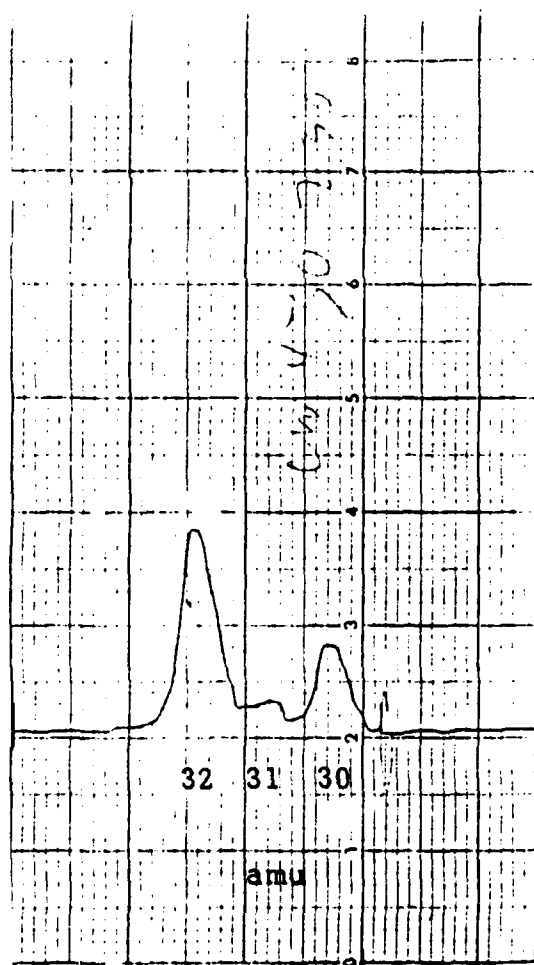


Fig. 10. Backbone disintegration of BAMO at 230 C, with production of CH_2O and CH_2OH at amu 30 and 31

relative concentrations of these species at 235 C compared with the azide N_2 evolution are shown in Figure 11.

B. Thermal Decomposition of Azido Copolymers

The thermal decomposition of several copolymers was investigated, including BAMO-AZOX, BAMO-AMMO, and BAMO-DNAO.

1. 50-50% BAMO-AZOX

Figure 12 shows the temperature dependence as measured by the N_2^+ intensity of the rate of nitrogen evolution resulting from the splitting of the $N-N_2$ bond of the azide group in the 50-50% BAMO-AZOX copolymer. The recording of these intensities (Fig. 12) shows a smooth increase in the rate of N_2 evolution as a function of temperature from 185 to 205 C. A semilog plot of these corrected nitrogen intensities versus the reciprocal of the absolute temperature yielded an activation energy of 176 kJ mol^{-1} (42.1 kcal/mole) for the copolymer (Fig. 13).

In addition to the release of nitrogen from the decomposition of the azide group, the 50-50% BAMO-AZOX copolymer shows decomposition of the polymeric backbone, as can be seen in Figure 14. This figure shows decomposition products with amu values of 27, 29, 30, 31, and 32 at 150 and 160 C. The probable species having these amu values are HCN, HCO, H_2CO and H_3CO , as well as molecular oxygen.

2. 50-50% BAMO-AMMO

The 50-50% BAMO-AMMO copolymer yielded a smooth nitrogen rate variation as a function of temperature. Figure 15 depicts the relative nitrogen intensities from 175 to 210 C. The corrected N_2 values when plotted against the reciprocal of the absolute temperature (Fig. 16) yielded an activation energy of 178 kJ mol^{-1} (42.5 kcal/mole) for the BAMO-AMMO copolymer. These results indicate that the thermal decomposition of the copolymers follows the same general mechanistic pattern as that of the homopolymers; that is, the splitting of the azide bond is the key factor in the mechanism for the thermal decomposition of the copolymers and the homopolymers.

3. 50-50% BAMO-DNAO

A new copolymer was recently prepared at SRI International involving BAMO with a nitrato ester, bis (nitrato methyl) oxetane, DNAO,

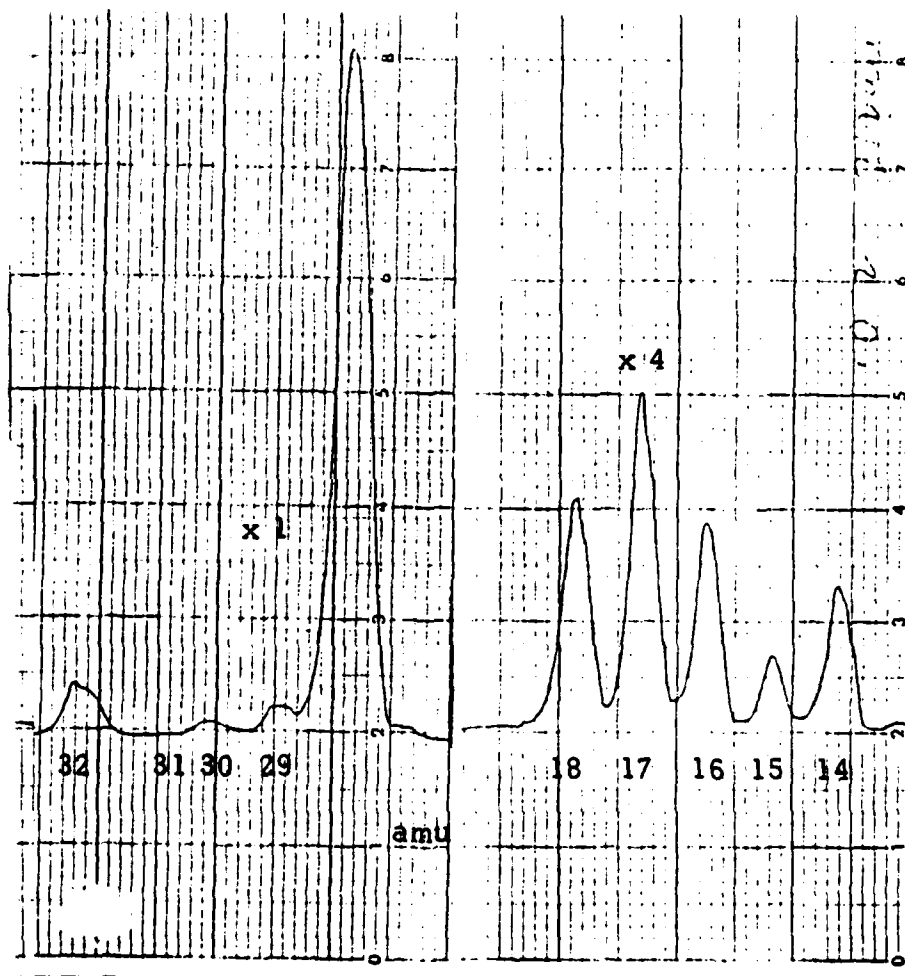


Fig. 11. Relative intensities of BAMO products at 235 C.
Species 14 - 18 intensities are magnified by a factor
of 4 over that of the N_2 intensities.

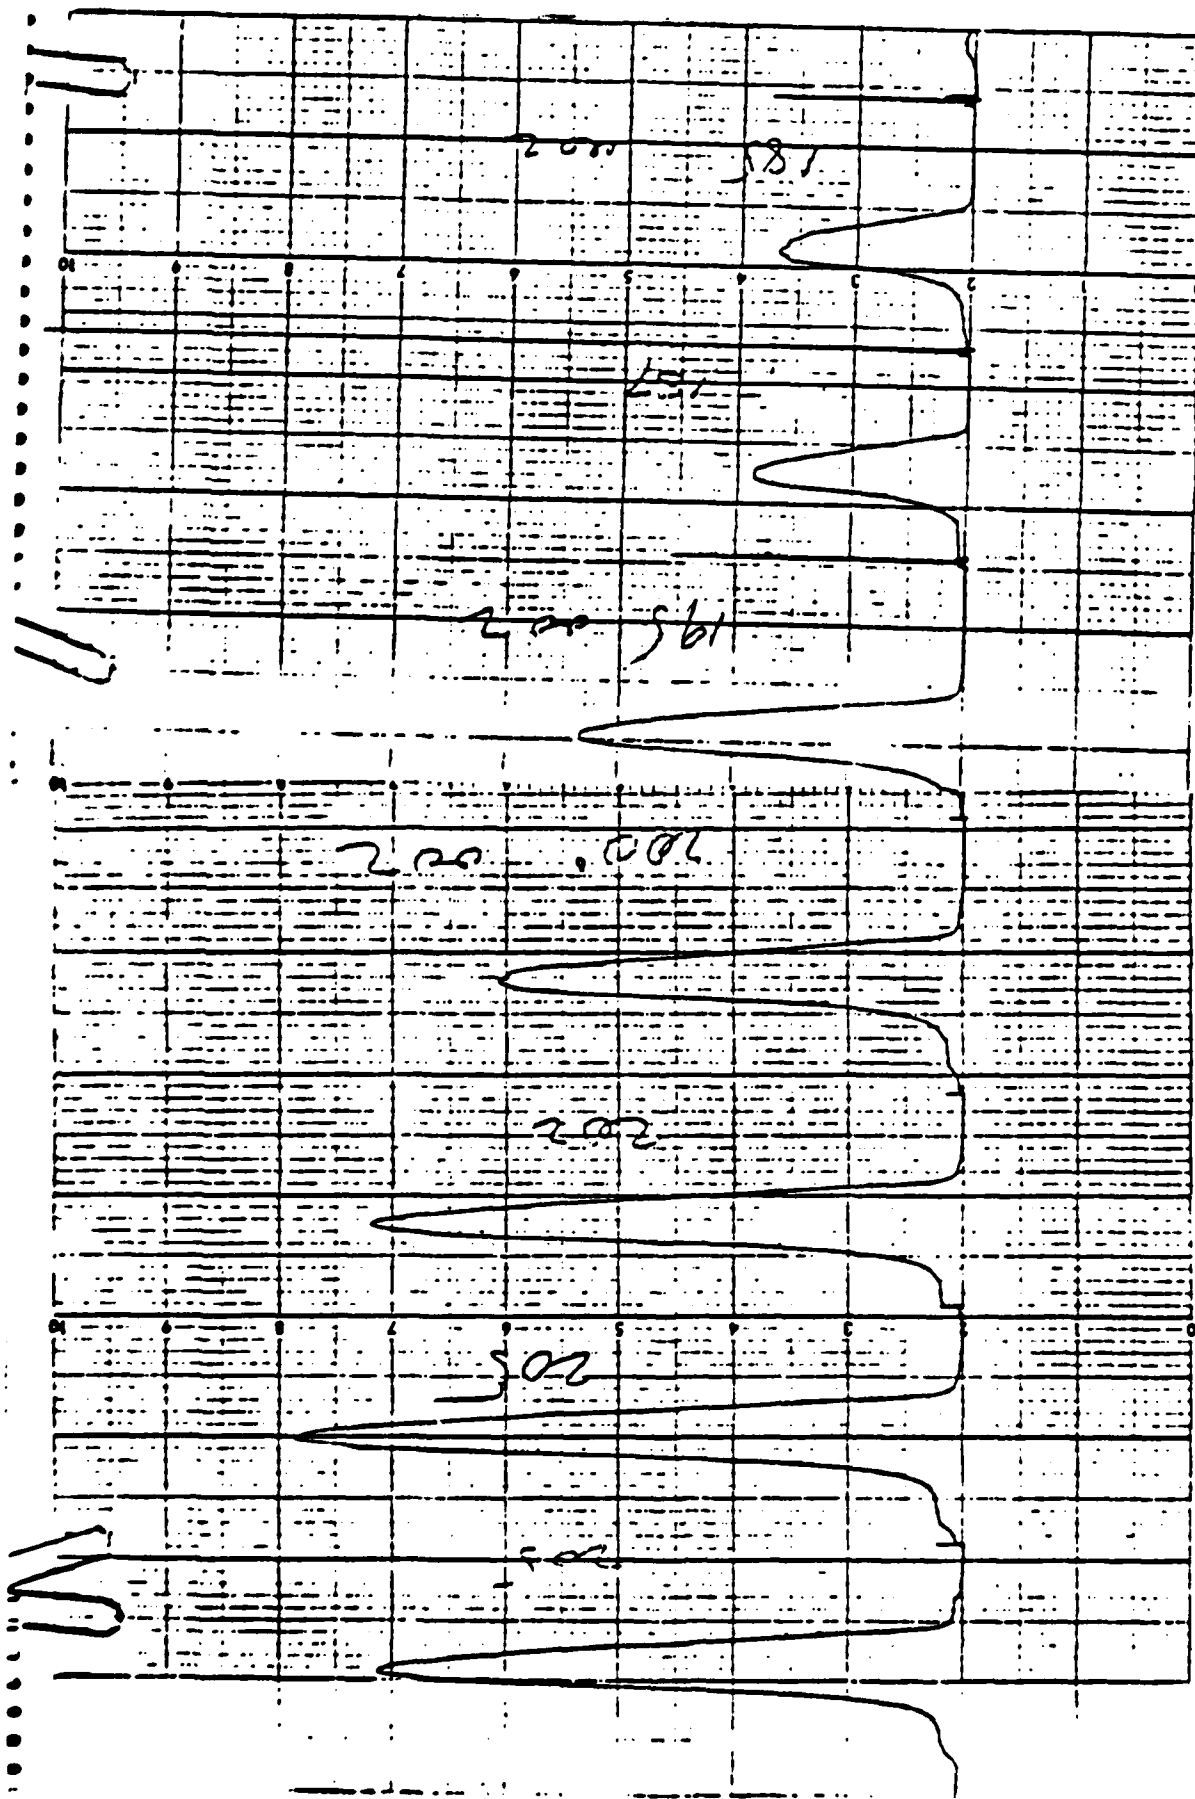


Fig. 12. Temperature dependence of the N_2 intensity (uncorrected) occurring from the thermal decomposition of 50%-50% BAMO-AZOX

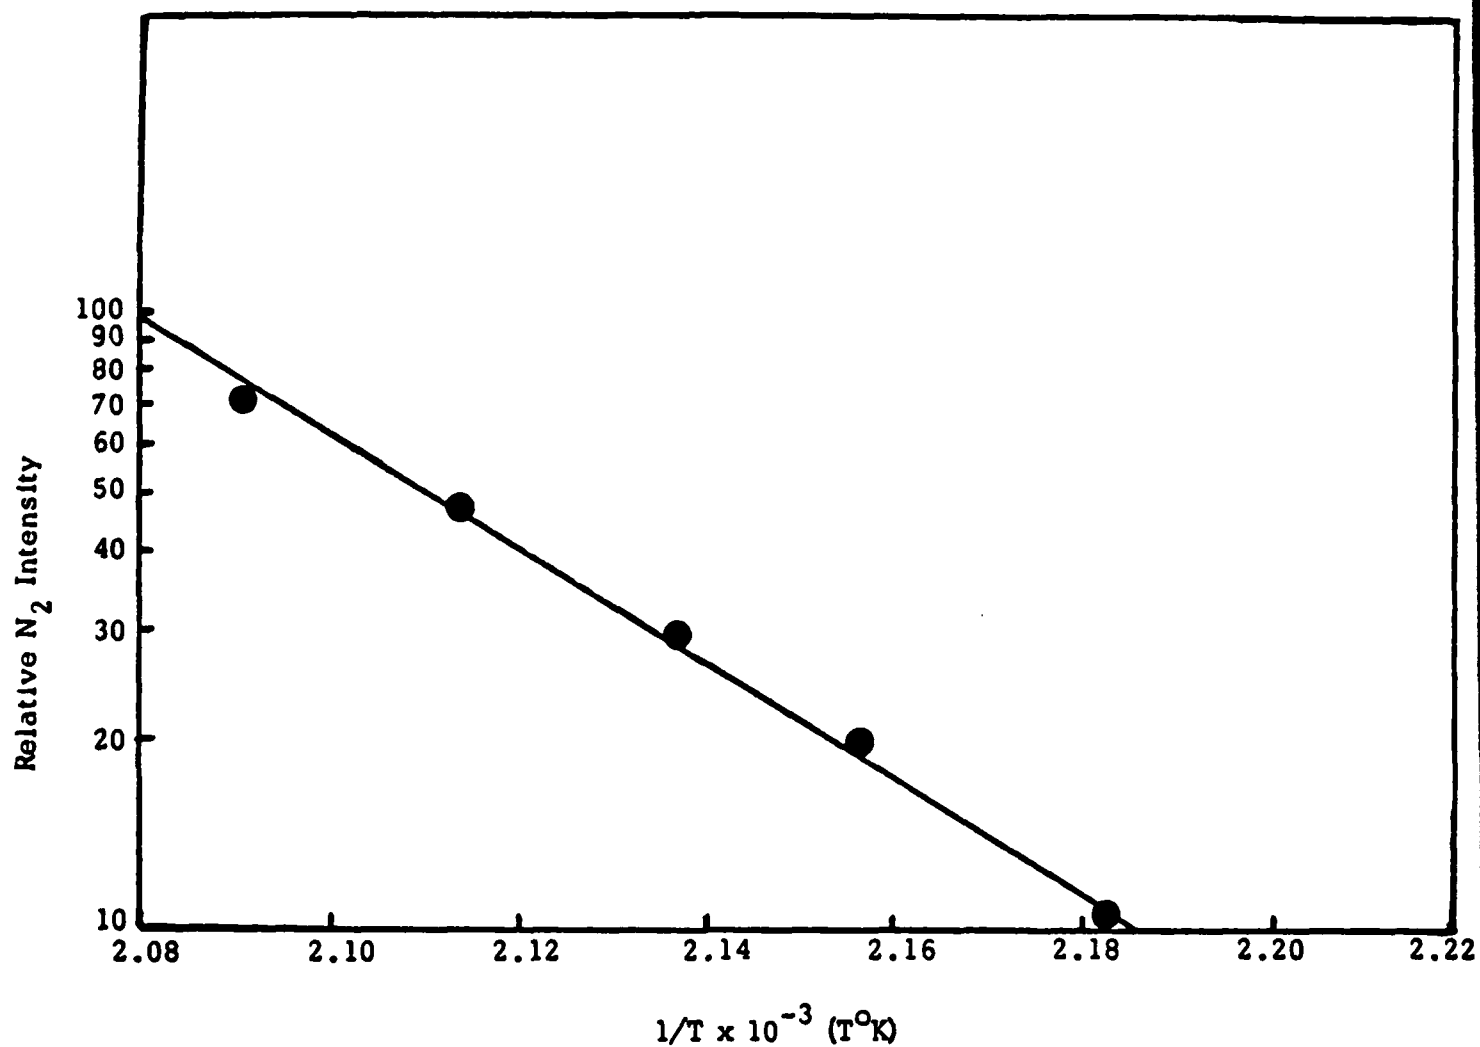


Fig. 13. Semilog plot of the N_2 intensity as a function of the reciprocal of the absolute temperature for the 50%-50% BAMO-AZOX copolymer. The E_a is 176 kJ/mole (42.1 kcal/mole)

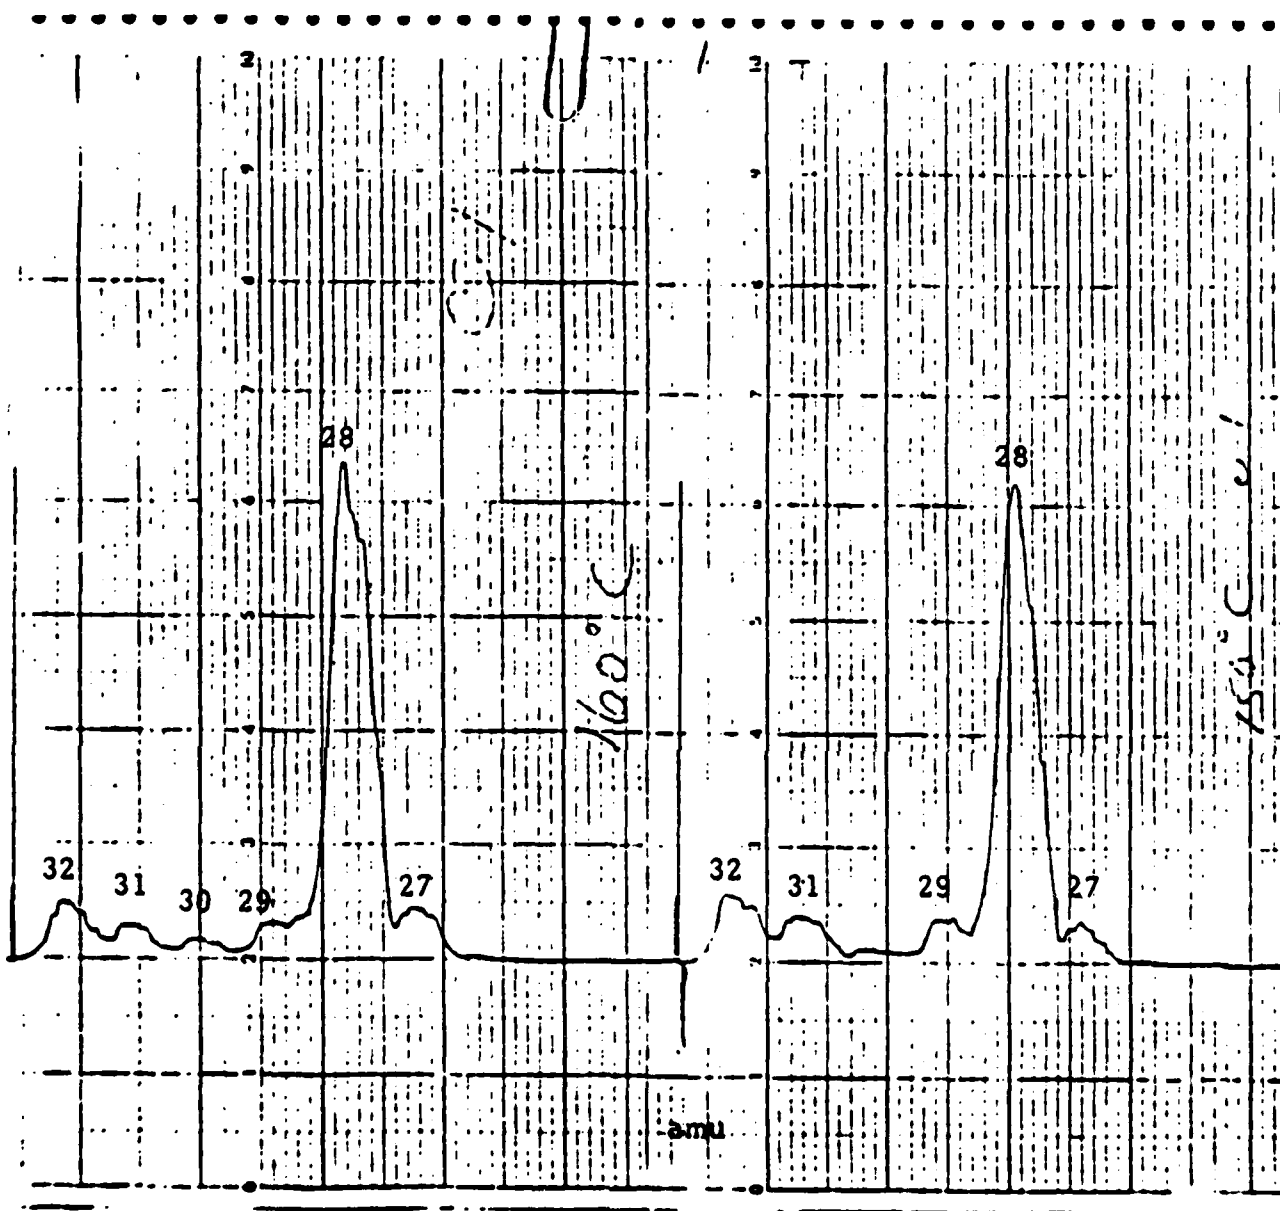


Fig. 14. Thermal decomposition of the 50%-50% BAMO-AZOX copolymer at 150 and 160 C

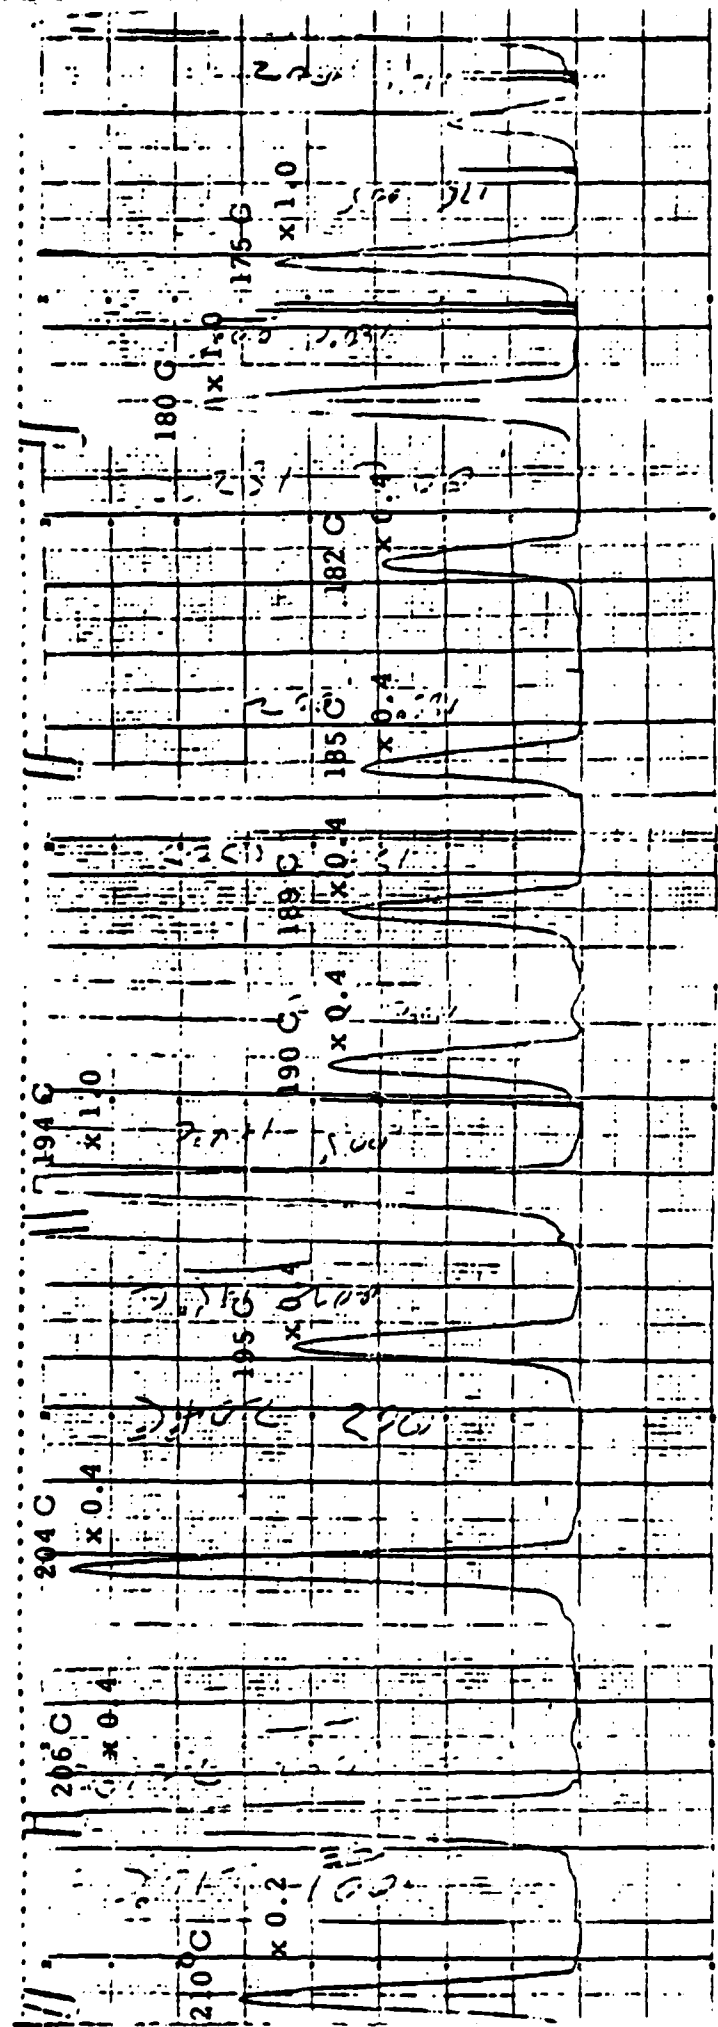


Fig. 15. Temperature dependence of the N_2 intensity (uncorrected) occurring from the thermal decomposition of 50%-50% BAMO-AMMO


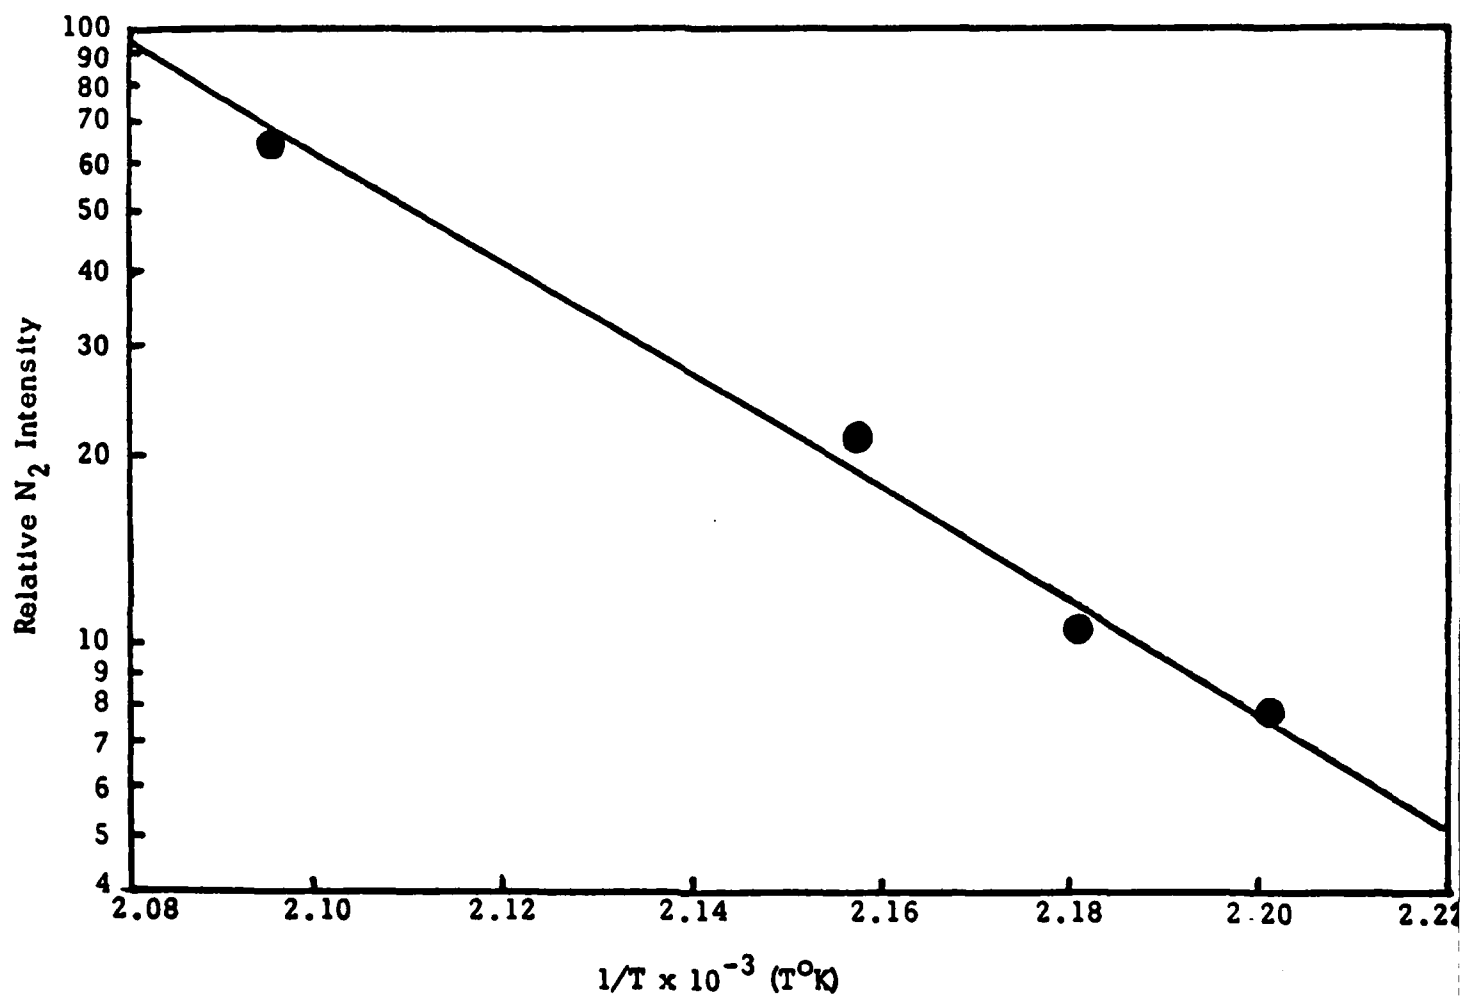


Fig. 16. Semilog plot of the N₂ intensity as a function of the reciprocal of the absolute temperature for the 50%-50% BAMO-AMMO copolymer. The E_a is 178 kJ/mole (42.5 kcal/mole).

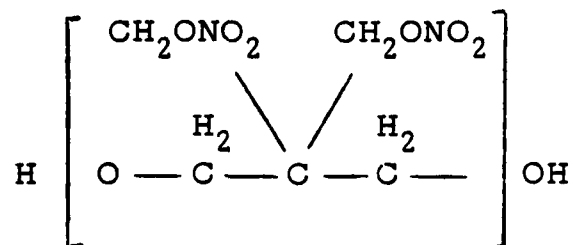


Unlike the copolymers of two azido compounds, this copolymer has two different reactant groups, an azide and nitrate.

The thermal decomposition mechanism of this copolymer is quite complicated in that both the azide and nitrate groups are initially decomposing at different rates. Figure 17 shows the decomposition products of this copolymer in the temperature range 110 to 208 C. Nitrate decomposition occurs well below that of the azido polymers, as shown by the prominent intensity peaks of 29, 30 and 31 amu arising from the CH_2ONO_2 group. As the temperature increases the rate of N_2 evolution from the BAMO decomposition is enhanced and agrees with the E_a for azide decomposition. Figure 18 shows the decomposition of 50-50% BAMO-DNAO as a function of three temperatures in three atomic mass ranges. At the lower temperature of 140 C the NO_2 peak is very pronounced due to the CH_2ONO_2 decomposition. At 200 C it has nearly disappeared. This can also be seen clearly from Figure 19, which shows the decreasing NO_2 concentration from 140 to 170 C.

Thermal decomposition studies on the homopolymer, as well as the copolymer of DNAO are continuing.

C. Thermal Decomposition of a New Energetic Amino-Nitro Ring Compound

A preliminary mass spectrometer study was made on a sample of the eight-membered C, N ring with NO_2 groups, having a molecular weight of 384, prepared at NSWC, White Oak

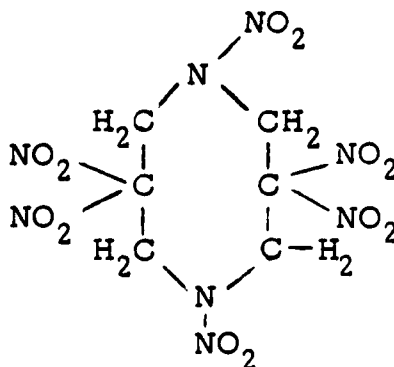

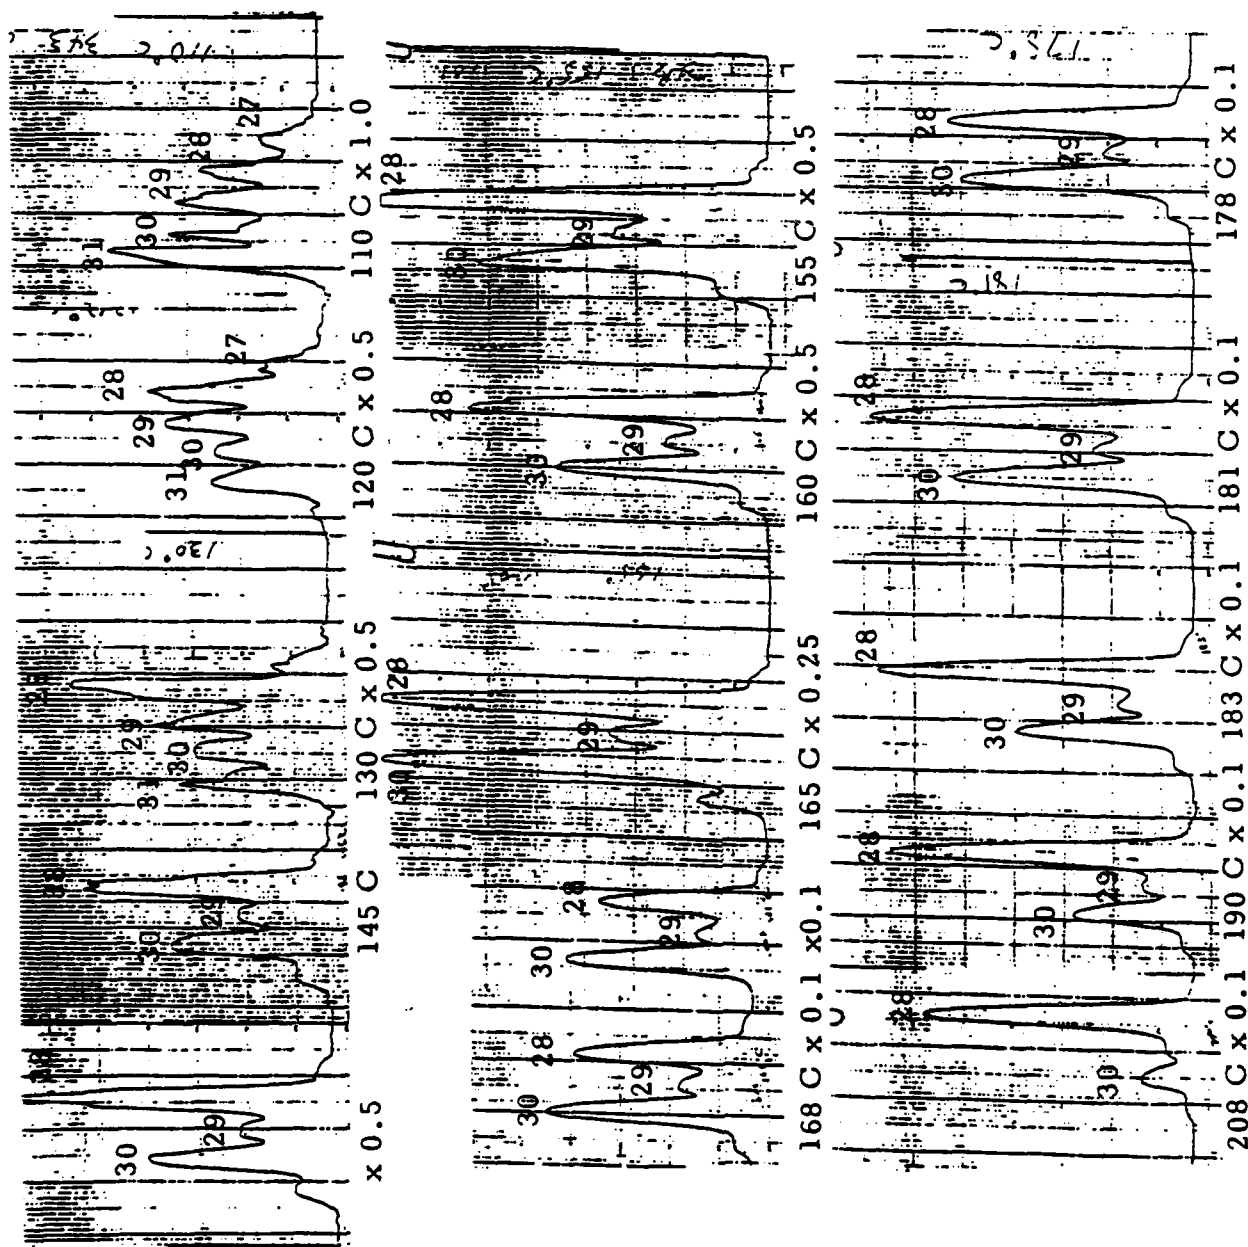


Fig. 17. Thermal decomposition of 50-50% BAMO-DNAO as a function of temperature

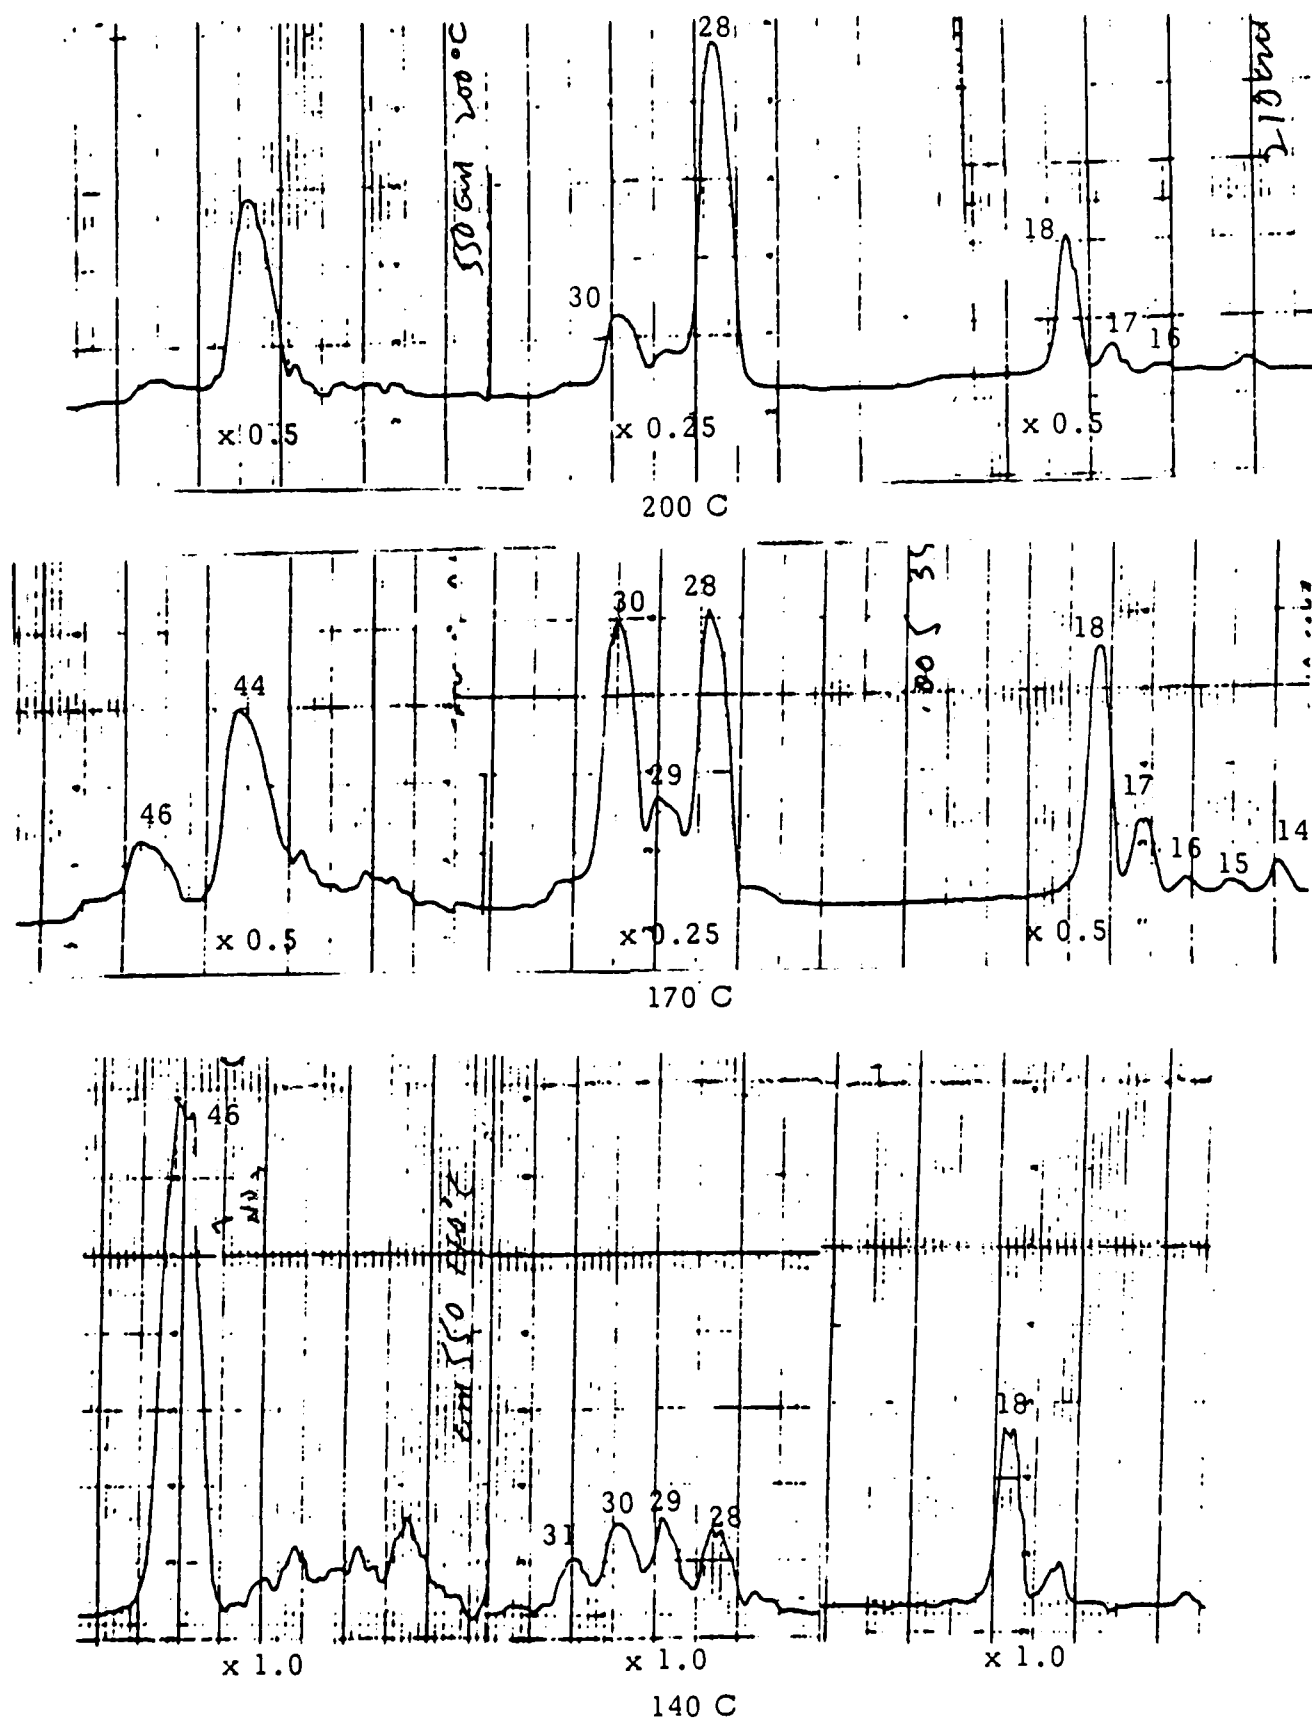


Fig. 18. Thermal decomposition of 50-50% BAMO-DNAO as a function of three temperatures in three amu ranges

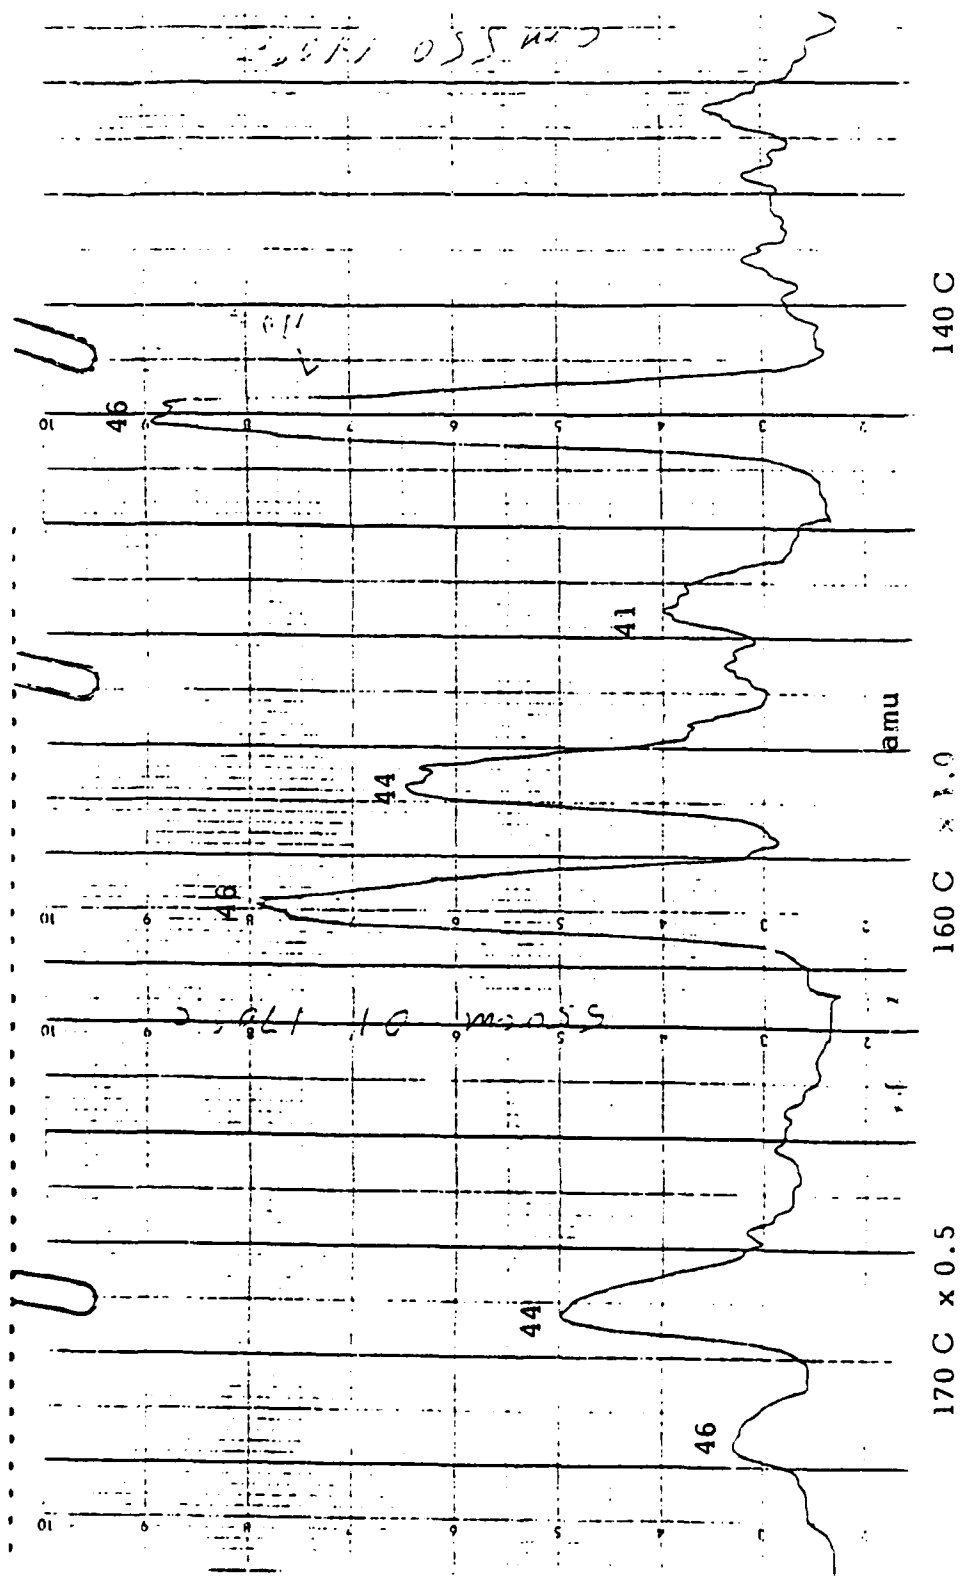


Fig. 19. Thermal decomposition of 50-50% BAMO-DNAO showing variation of species in the 40 - 46 amu range

The initial decomposition product of this compound is NO_2 , which appears at approximately 150 C. A semilog plot of the NO_2 intensity (Fig. 20) yields an approximate activation energy of 165 kJ mol^{-1} (40 kcal/mole). The ring itself appears to be stable, with only NO_2 release. For example, at 260 C (Fig. 21) the most prominent peak observed is at 292 amu, which corresponds to the molecule (amu 384) less two NO_2 groups. The next highest intensity peak is observed at 200 amu, corresponding to the molecule less four NO_2 groups. It is possible that the molecule is evaporating as well as decomposing, since Figure 21 also shows a very low concentration ion intensity of 384 amu which corresponds to the compound itself. However, since this peak is barely discernible above the noise level, it should not be definitely construed that the molecules does undergo evaporation. More experiments will be conducted on this molecule.

III. ULTRAVIOLET STUDIES

There has been some concern in the propellant community regarding the sensitivity of the new azido polymers to sunlight degradation, especially the ultraviolet, and also, if decomposition were initiated, whether it would continue as a result of autocatalysis. A series of qualitative ultraviolet decomposition studies was conducted in an attempt to answer these questions. The materials investigated were the homopolymers of AZOX and AMMO and the copolymers 50-50% BAMO-AZOX and 50-50% BAMO-AMMO.

Two types of UV lamps were employed, a short wave of 2540 \AA and a long wave of 3660 \AA . The radiation obtained from these lamps is 7.83×10^{-19} joules/photon, equivalent to 4.88 eV, for the short wave, and 5.43×10^{-19} joules/photon, equivalent to 3.39 eV, for the long wave. These energies correspond to 112 kcal/mole and 78 kcal/mole, respectively, for the short and long wave UV lamps. The deposition energy at a distance of 1 inch from the surface to be irradiated is 7200 uwatts/cm^2 and $10,000 \text{ uwatts/cm}^2$ for the short and long wave lamps.

The first material studied was the AZOX homopolymer employing both the short and long wave UV radiation. Samples of the polymer of

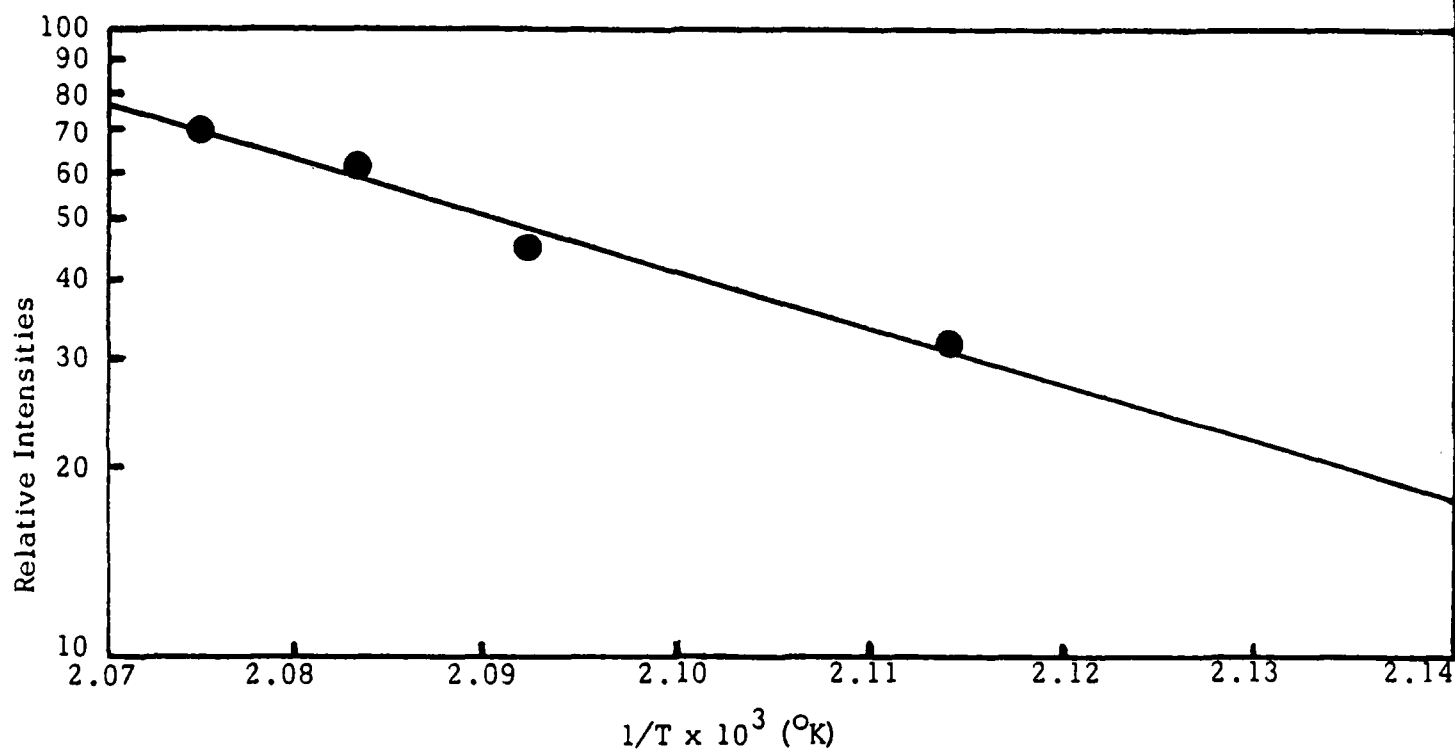


Fig. 20. Activation energy based on NO_2 ion intensities for the new NSWC compound

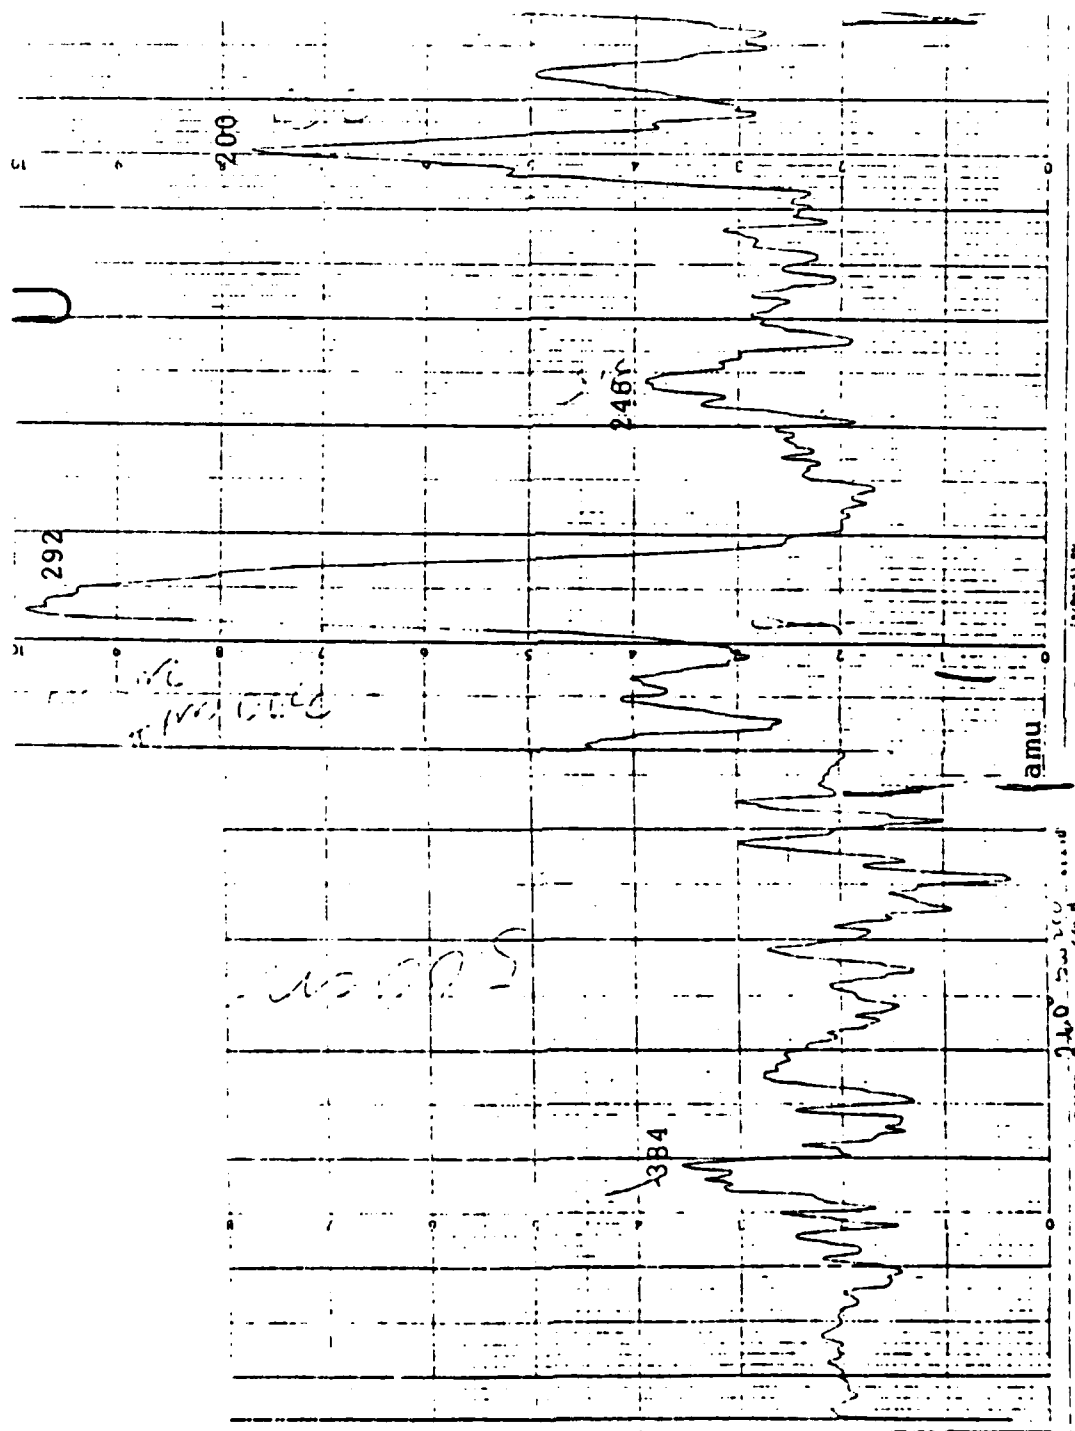


Fig. 21. Principal decomposition fragments observed from the thermal decomposition of the NSWC compound at 260 C

approximately 25 mg in weight were placed in a 1 cm^2 area on aluminum foil at a distance of 1 inch from the UV lamp.

After several preliminary experiments with the short wave 2540 \AA ultraviolet they were discontinued due to considerable adsorption of the short wave radiation caused by its path through the air. Short wave UV irradiation studies would thus best be accomplished in a vacuum enclosure.

The results for both the long and short wave radiation involving the AZOX homopolymer are shown in Figure 22. Considerable decomposition was observed in relatively short times. As can be seen approximately 4% and 8% reduction in the sample weight was accomplished in a one-hour irradiation. The nitrogen content of AZOX is 42%, whereas the N_2 of the azide group is only 28%. Thus in a five-hour exposure to UV 3660 \AA radiation between one-third and one-half of the N_2 content of the polymer was released. Visual observation of the polymer after irradiation revealed that the material changed from viscous liquid to a gummy, or rubbery, semi-solid. In order to determine whether ordinary light would cause decomposition, a sample of the AZOX polymer was exposed to fluorescent light for five days; there was no apparent weight loss.

Experiments on the AMMO homopolymer, the 50-50% BAMO-AZOX, and the 50-50% BAMO-AMMO copolymers were performed with the 3660 \AA long wave lamp. The samples were irradiated at distances of 1" ($10,000\text{ }\mu\text{watts/cm}^2$), 3" ($1120\text{ }\mu\text{watts/cm}^2$), and 6" ($380\text{ }\mu\text{watts/cm}^2$) for periods up to five hours. The radiation intensity, for example, at a distance of 1" from the sample surface provides 36 J/cm^2 for each hour of exposure. The decomposition rate of the AMMO homopolymer (Fig. 23) appears to be similar to that of the AZOX homopolymer as shown in Figure 22.

Qualitative results for the copolymers are shown in Figure 24. In all cases the irradiated samples show considerable gas release with polymeric cross-linking producing rubbery solids from the initial viscous liquids. The irradiated samples (homopolymers and copolymers) were maintained for a number of weeks under ordinary atmospheric conditions as well as under vacuum. No autocatalysis was observed.

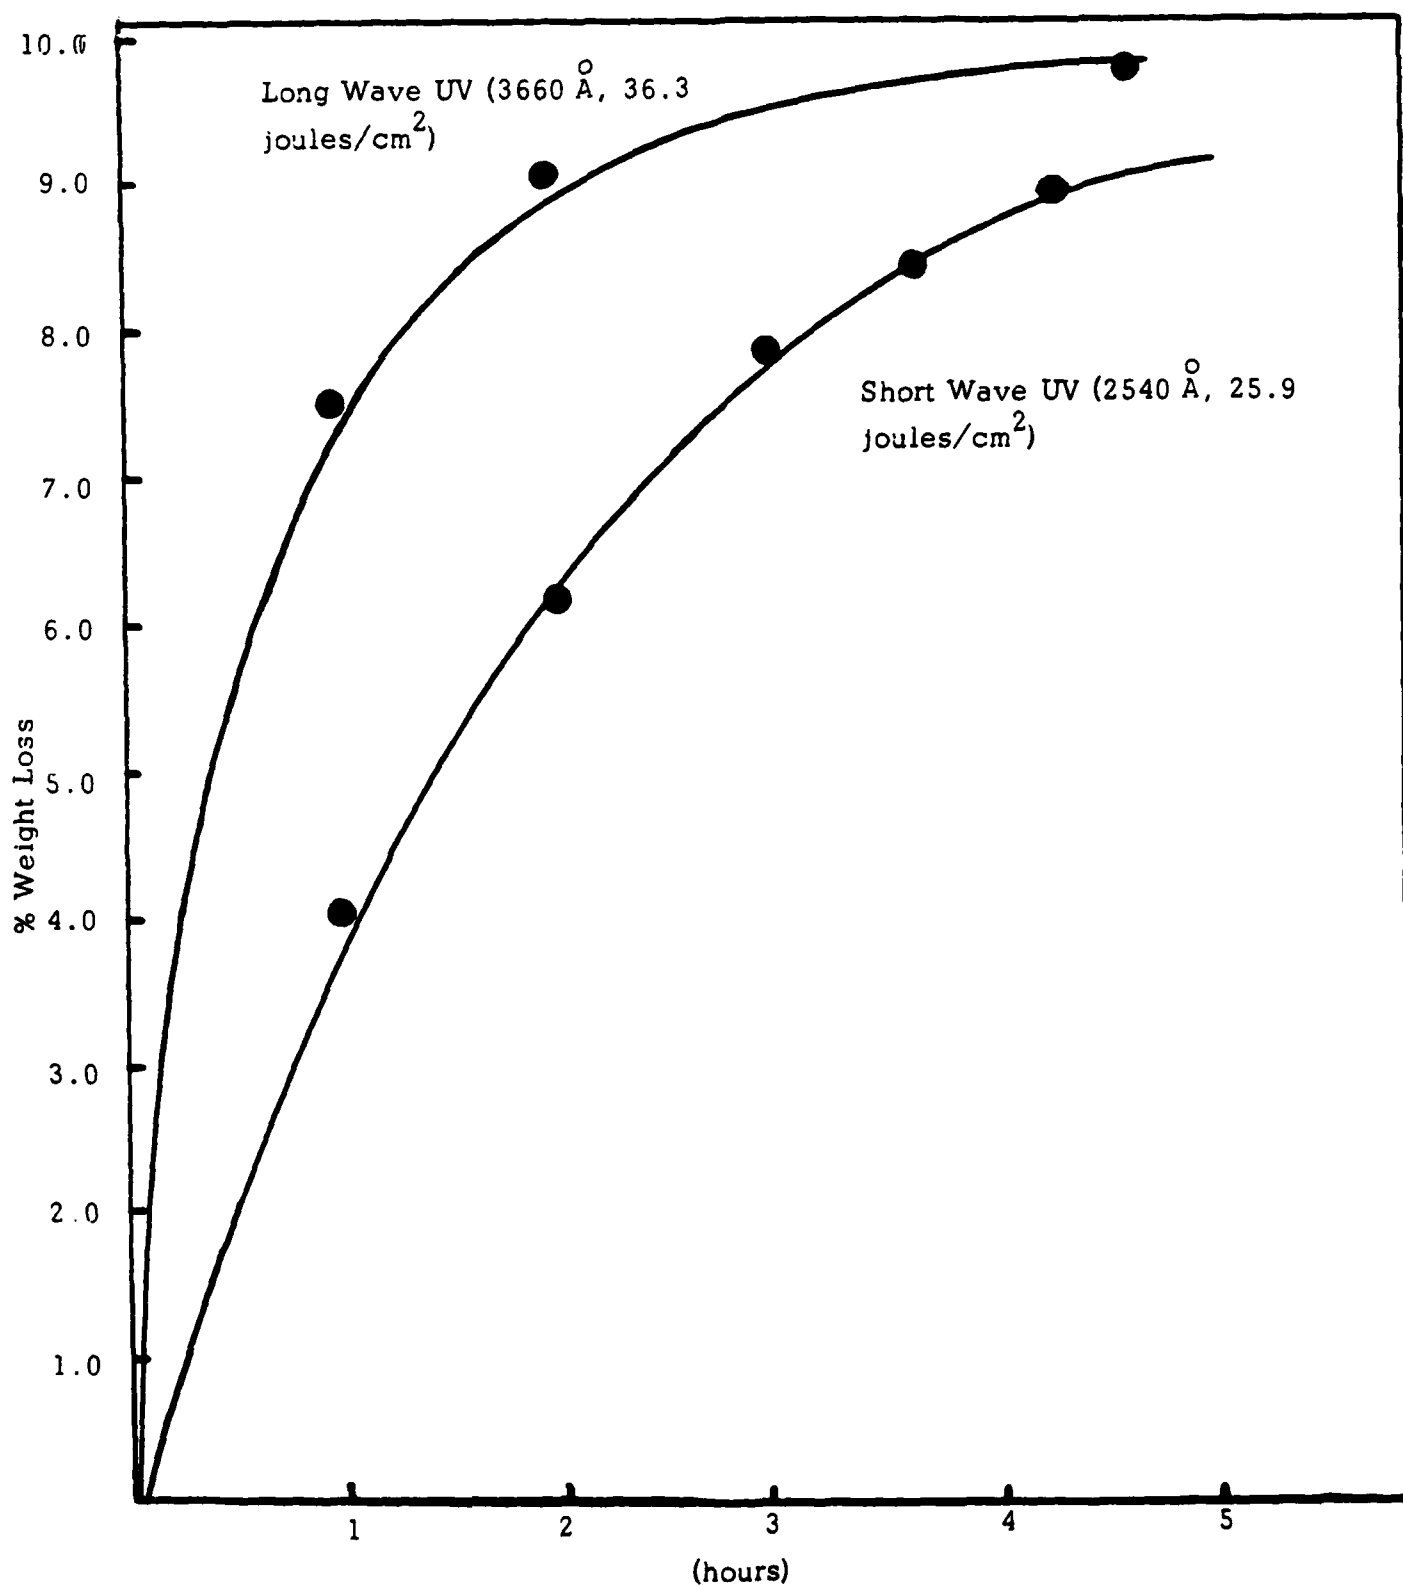


Fig. 22. Ultraviolet irradiation of AZOX polymer sample size 20 mg on 1 cm² area

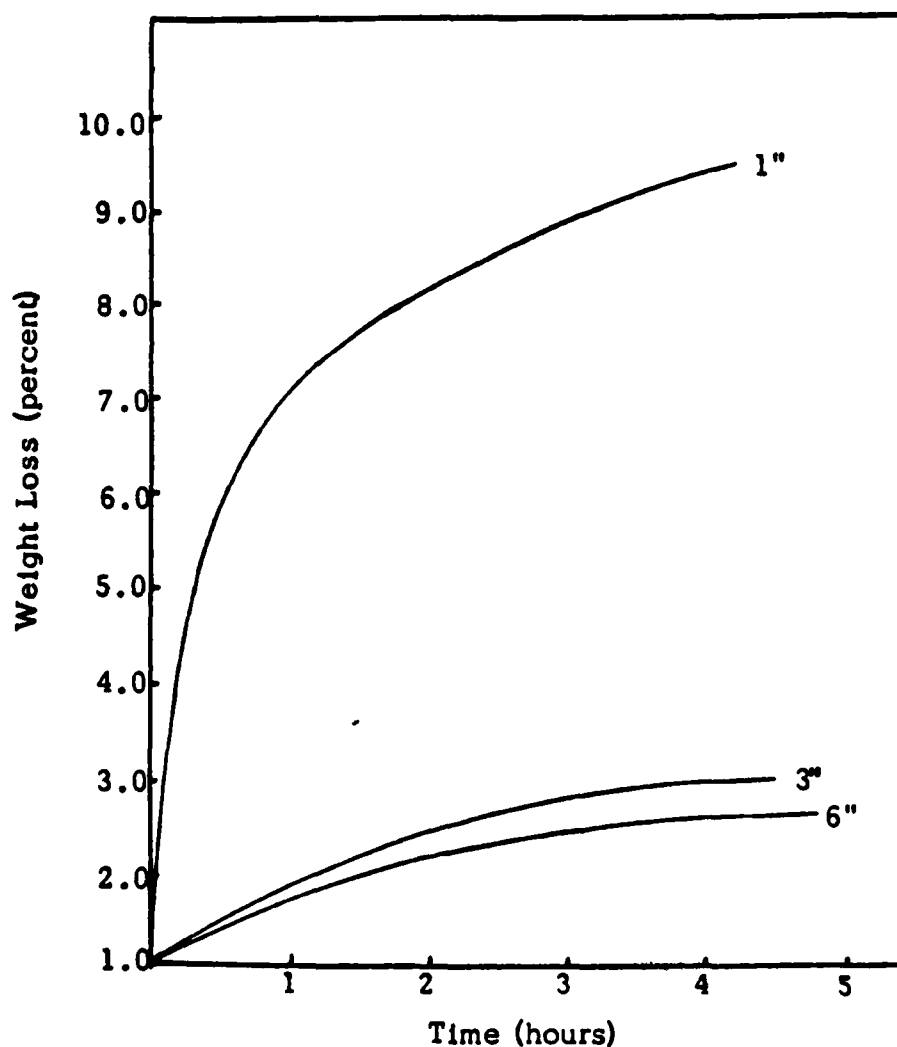


Fig. 23. Weight loss of the AMMO homopolymer as a function of long wave (3660\AA) ultraviolet radiation at distances of 1" ($10,000\text{ }\mu\text{watts/cm}^2$), 3" ($1120\text{ }\mu\text{watts/cm}^2$), and 6" ($380\text{ }\mu\text{watts/cm}^2$) from the sample surface. The intensity of the radiation is 3.39 eV (78 kcal/mole).

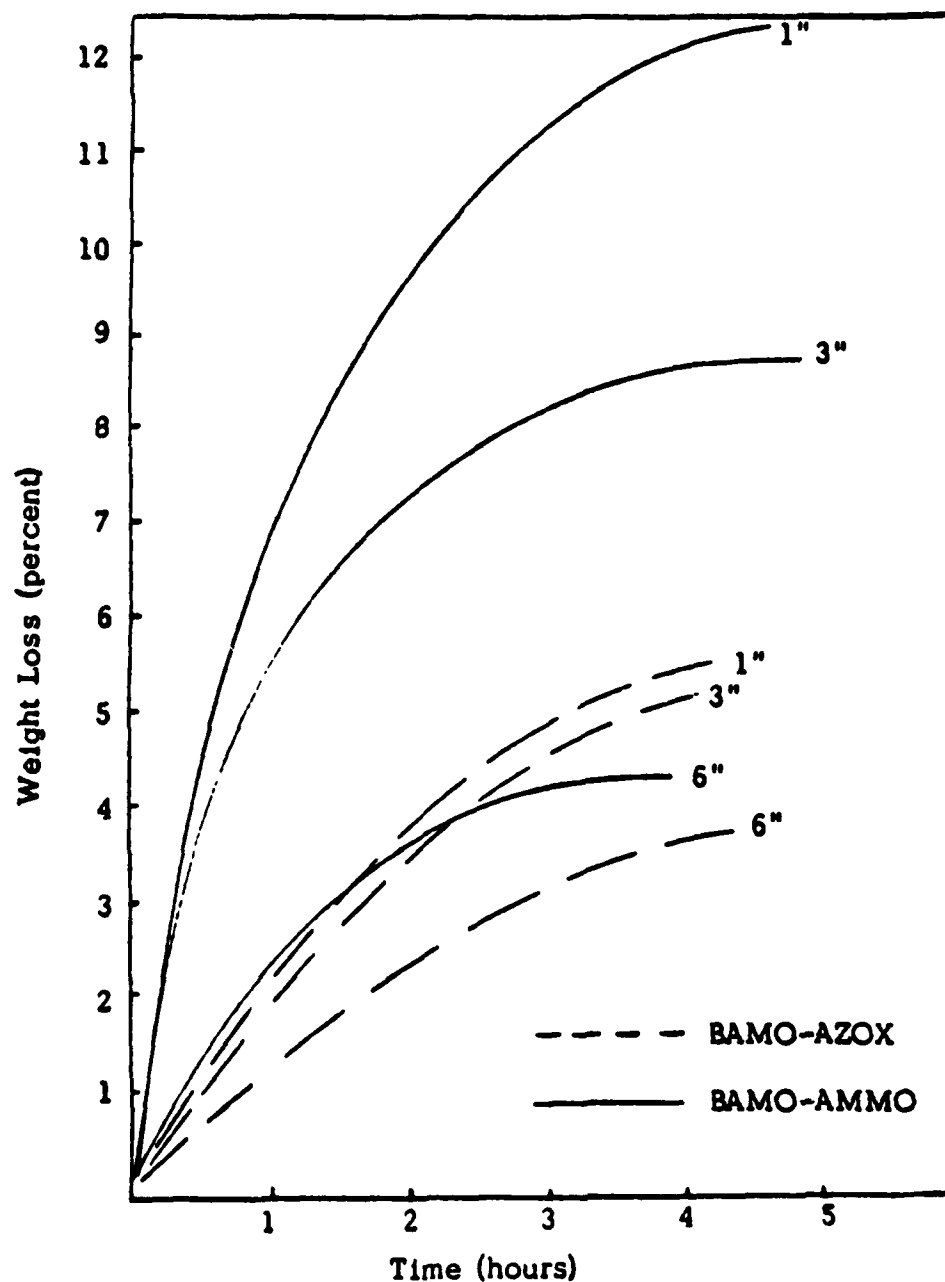


Fig. 24. Weight loss of the BAMO-AZOX and BAMO-AMMO copolymers as a function of long wave (3660\AA) ultraviolet radiation at distances of 1" ($10,000 \mu\text{watts/cm}^2$), 3" ($1120 \mu\text{watts/cm}^2$), and 6" ($380 \mu\text{watts/cm}^2$) from the sample surface. The intensity of the radiation is 3.39 eV (78 kcal/mole).

INT.

ENERGETIC MATERIALS RESEARCHDISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Assistant Secretary of the Navy (R, E, and S) Attn: Dr. R.E. Reichenbach Room 5E787 Pentagon Washington, DC 20350	1	AFATL Eglin AFB, FL 32542 Attn: Dr. Otto K. Heiney	1
Office of Naval Research Code 473 Arlington, VA 22217 Attn: Dr. R. Miller	10	AFRPL Code PACC Edwards AFB, CA 93523 Attn: Mr. W. C. Andrepont	1
Office of Naval Research Code 200B Arlington, VA 22217 Attn: Dr. J. Enig	1	AFRPL Code CA Edwards AFB, CA 93523 Attn: Dr. R. R. Weiss	1
Office of Naval Research Code 260 Arlington, VA 22217 Attn: Mr. D. Siegel	1	Code AFRPL MKPA Edwards AFB, CA 93523 Attn: Mr. R. Geisler	1
Office of Naval Research Western Office 1030 East Green Street Pasadena, CA 91106 Attn: Dr. T. Hall	1	Code AFRPL MKPA Edwards AFB, CA 93523 Attn: Dr. F. Roberto	1
Office of Naval Research Eastern Central Regional Office 495 Summer Street Boston, MA 02210 Attn: Dr. L. Peebles Dr. A. Wood	2	AFSC Andrews AFB, Code DLFP Washington, DC 20334 Attn: Mr. Richard Smith	1
Office of Naval Research San Francisco Area Office One Hallidie Plaza Suite 601 San Francisco, CA 94102 Attn: Dr. P. A. Miller	1	Air Force Office of Scientific Research Directorate of Chemical & Atmospheric Sciences Bolling Air Force Base Washington, DC 20332	1
Defense Technical Information Center DTIC-DDA-2 Cameron Station Alexandria, VA 22314	12	Air Force Office of Scientific Research Directorate of Aero- space Sciences Bolling Air Force Base Washington, DC 20332 Attn: Dr. L. H. Caveny	1
		Anal-Syn Lab Inc. P.O. Box 547 Paoli, PA 19301 Attn: Dr. V. J. Keenan	1

	<u>No. Copies</u>		<u>No. Copies</u>
Army Ballistic Research Labs Code DRDAR-BLP Aberdeen Proving Ground, MD 21005 Attn: Mr. L. A. Watermeier	1	Hercules Inc. Eglin AFATL/DLDL Eglin AFB, FL 32542 Attn: Dr. Ronald L. Simmons	1
Army Ballistic Research Labs ARRADCOM Code DRDAR-BLP Aberdeen Proving Ground, MD 21005 Attn: Dr. Ingo W. May	1	Hercules Inc. Magna Bacchus Works P.O. Box 98 Magna, UT 84044 Attn: Mr. E. H. DeButts	1
Army Ballistic Research Labs ARRADCOM Code DRDAR-BLT Aberdeen Proving Ground, MD 21005 Attn: Dr. Philip Howe	1	Hercules Inc. Magna Bacchus Works P.O. Box 98 Magna, UT 84044 Attn: Dr. James H. Thacher	1
Army Missile Command Code DRSME-RK Redstone Arsenal, AL 35809 Attn: Dr. R. G. Rhoades Dr. W. W. Wharton	2	HQ US Army Material Development Readiness Command Code DRCDE-DW 5011 Eisenhower Avenue Room 8N42 Alexandria, VA 22333 Attn: Mr. S. R. Matos	1
Atlantic Research Corp. 5390 Cherokee Avenue Alexandria, VA 22314 Attn: Dr. C. B. Henderson	1	Johns Hopkins University APL Chemical Propulsion Information Agency Johns Hopkins Road Laurel, MD 20810 Attn: Mr Theodore M. Gilliland	1
Ballistic Missile Defense Advanced Technology Center P.O. Box 1500 Huntsville, AL 35807 Attn: Dr. David C. Sayles	1	Lawrence Livermore Laboratory University of California Livermore, CA 94550 Attn: Dr. M. Finger	1
Ballistic Research Laboratory USA ARRADCOM DRDAR-BLP Aberdeen Proving Ground, MD 21005 Attn: Dr. A. W. Barrows	1	Lawrence Livermore Laboratory University of California Livermore, CA 94550 Attn: Dr. R. McGuire	1
Hercules Inc. Cumberland Aerospace Division Allegany Ballistics Lab P.O. Box 210 Cumberland, MD 21502 Attn: Dr. Rocco Musso	2	Lockheed Missiles and Space Co. P.O. Box 504 Sunnyvale, CA 94088 Attn: Dr. Jack Linsk Org. 83-10 Bldg. 154	1

	<u>No. Copies</u>		<u>No. Copies</u>
Lockheed Missile & Space Co. 3251 Hanover Street Palo Alto, CA 94304 Attn: Dr. H. P. Marshall Dept. 52-35	1	Naval Research Lab Code 6100 Washington, DC 20375	1
Los Alamos Scientific Lab P.O. Box 1663 Los Alamos, NM 87545 Attn: Dr. R. Rogers, WX-2	1	Naval Sea Systems Command Washington, DC 20362 Attn: Mr. G. Edwards, Code 62R3 Mr. J. Murrin, Code 62R2 Mr. W. Blaine, Code 62R	1
Los Alamos Scientific Lab P.O. Box 1663 Los Alamos, NM 87545 Attn: Dr. B. Craig, M Division	1	Naval Sea Systems Command Washington, DC 20362 Attn: Mr. R. Beauregard SEA 64E	1
Naval Air Systems Command Code 330 Washington, DC 20360 Attn: Mr. R. Heitkotter Mr. R. Brown	1	Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910 Attn: Dr. H. G. Adolph	1
Naval Air Systems Command Code 310 Washington, DC 20360 Attn: Dr. H. Mueller Dr. H. Rosenwasser	1	Naval Surface Weapons Center Code R13 White Oak, Silver Spring, MD 20910 Attn: Dr. R. Bernecker	1
Naval Explosive Ordnance Disposal Facility Indian Head, MD 20640 Attn: Lionel Dickinson Code D	1	Naval Surface Weapons Center Code R10 White Oak, Silver Spring, MD 20910 Attn: Dr. S. J. Jacobs	1
Naval Ordnance Station Code 5034 Indian Head, MD 20640 Attn: Mr. S. Mitchell	1	Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910 Attn: Dr. M. J. Kamlet	1
Naval Ordnance Station Code PM4 Indian Head, MD 20640 Attn: Mr. C. L. Adams	1	Naval Surface Weapons Center Code R04 White Oak, Silver Spring, MD 20910 Attn: Dr. D. J. Pastine	1
Dean of Research Naval Postgraduate School Monterey, CA 93940 Attn: Dr. William Tolles	1	Naval Surface Weapons Center Code R13 White Oak, Silver Spring, MD 20910 Attn: Dr. E. Zimet	1
Naval Research Lab Code 6510 Washington, DC 20375 Attn: Dr. J. Schnur	1		

	<u>No. Copies</u>		<u>No. Copies</u>
Naval Surface Weapons Center Code R101 Indian Head, MD 20640 Attn: Mr. G. L. MacKenzie	1	Naval Weapons Center Code 388 China Lake, CA 93555 Attn: D. R. Derr	1
Naval Surface Weapons Center Code R17 Indian Head, MD 20640 Attn: Dr. H. Haiss	1	Naval Weapons Center Code 388 China Lake, CA 93555 Attn: Dr. R. Reed Jr.	1
Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910 Attn: Dr. K. F. Mueller	1	Naval Weapons Center Code 385 China Lake, CA 93555 Attn: Dr. A. Nielsen	1
Naval Surface Weapons Center Code R16 Indian Head, MD 20640 Attn: Dr. T. D. Austin	1	Naval Weapons Center Code 3858 China Lake, CA 93555 Attn: Mr. E. Martin	1
Naval Surface Weapons Center Code R122 White Oak, Silver Spring, MD 20910 Attn: Mr. L. Roslund	1	Naval Weapons Center China Lake, CA 93555 Attn: Mr. R. McCarten	1
Naval Surface Weapons Center Code R121 White Oak, Silver Spring, MD 20910 Attn: Mr. M. Stosz	1	Naval Weapons Support Center Code 5042 Crane, Indiana 47522 Attn: Dr. B. Douda	1
Naval Weapons Center Code 3853 China Lake, CA 93555 Attn: Dr. R. Atkins	1	Rohm and Haas Company 723-A Arcadia Circle Huntsville, Alabama 35801 Attn: Dr. H. Shuey	1
Naval Weapons Center Code 3205 China Lake, CA 93555 Attn: Dr. L. Smith	1	Strategic Systems Project Office Dept. of the Navy Room 901 Washington, DC 20376 Attn: Dr. J. F. Kincaid	1
Naval Weapons Center Code 3205 China Lake, CA 93555 Attn: Dr. C. Thelen	1	Strategic Systems Project Office Dept. of the Navy Room 1048 Washington, DC 20376 Attn: Mr. E. L. Throckmorton Mr. R. Kinert	2
Naval Weapons Center Code 385 China Lake, CA 93555 Attn: Dr. A. Amster	1	Thiokol Chemical Corp. Brigham City Wasatch Division Brigham City, UT 84302 Attn: Dr. G. Thompson	1

	<u>No. Copies</u>		<u>No. Copies</u>
USA ARRADCOM DRDAR-LCE Dover, NJ 07801 Attn: Dr. R. F. Walker	1	University of California Department of Chemistry 405 Hilgard Avenue Los Angeles, CA 90024 Attn: Professor M. Nicol	1
USA ARRADCOM DRDAR-LCE Dover, NJ 07801 Attn: Dr. N. Slagg	1	University of California Energy Center Mail Code B-010 La Jolla, CA 92093 Attn: Prof. S.S. Penner	1
U.S. Army Research Office Chemistry Division P.O. Box 12211 Research Triangle Park, NC 27709	1	University of Washington Department of Chemistry Seattle, Washington 98195 Attn: Prof. B.S. Rabinovitch	1
Washington State University Dept. of Physics Pullman, WA 99163 Attn: Professor G.D. Duval	1	Dr. P. Rentzepis Bell Laboratories Murray Hill N.J. 07971	1
Space Sciences, Inc. 135 West Maple Avenue Monrovia, CA 91016 Attn: Dr. M. Farber	1	University of Southern CA Department of Electrical Engineering University Park Los Angeles, CA 90007 Attn: C. Wittig	1
SRI International 333 Ravenswood Avenue Menlo Park, CA 94025 Attn: Mr. M. Hill	1	MIT Dept. of Chemistry Cambridge, MA 02139 Attn: Prof. John Deutsch	
Office of Naval Research Code 421 Arlington, VA 22217 Attn: Dr. B. Junker	1		
The Johns Hopkins University Department of Chemistry Baltimore, MD 21218 Attn: Dr. Joyce J. Kaufman	1		
University of California Department of Chemistry Berkeley, CA 94720 Attn: Professor Y.T. Lee	1		
Office of Naval Research Code 472 Arlington, VA 22217 Attn: Dr. G. Neece	1		

END

FILMED

1-83

DTIC